



Tikrit Journal of Pure Science

ISSN: 1813 – 1662 (Print) --- E-ISSN: 2415 – 1726 (Online)

Journal Homepage: <http://tjps.tu.edu.iq/index.php/j>



Green synthesis of Silver Nanoparticles using the extract of *Rheum ribes* and evaluating their antifungal activity against some of *Candida sp.*

Mustafa Mahdi Auda, Hajir Ali Shareef, Bari Lateef Mohammed

Department of Biology, College of Science, University of Kirkuk, Kirkuk, Iraq

DOI: <http://dx.doi.org/10.25130/tjps.26.2021.028>

ARTICLE INFO.

Article history:

-Received: 4 / 12 / 2020

-Accepted: 15 / 12 / 2020

-Available online: / / 2021

Keywords: Silver nanoparticles, Green synthesis, *Rheum ribes*, Antifungal

Corresponding Author:

Name: Mustafa Mahdi Auda

E-mail: mmauda92@gmail.com

Tel:

ABSTRACT

The synthesis of nanoparticles by green method using plant extracts and its application in the biomedical consider a prosperous field of research. Therefore, in this paper, Rheum plant was used as a reducing agent in synthesis silver nanoparticles and testing its effectiveness as anti-fungal. Silver Nanoparticles have been characterized using different techniques such as UV-visible spectroscopy, X-ray diffraction, Fourier transforms infrared spectroscopy and transmission electron microscope. Where the result of the examination UV-Vis showed absorption peaks of silver nanoparticles which formatted at wavelength (425) and XRD test confirmed the presence of silver nanoparticles clearly through compare peaks resulted with JCPDS card. It revealed the spectra of FTIR the existence of amine and aliphatic esters, that are involved in reducing and stabilizing AgNPs. Examination of TEM revealed that the silver nanoparticles were spherical shape and with an average size of 5-45 nm. Finally, the synthesized silver nanoparticles showed a good antifungal activity against some *Candida sp.* by observe inhibition zones that obtained.

Introduction

The nanotechnology field is one of the most active research areas in modern materials science. Nanoparticles display new or improved properties based on specific characteristics such as size, distribution, and morphology [1]. In the recent past years, there have been impressive developments in the nanotechnology fields, with numerous approaches developed to synthesize nanoparticles of particular shape and size depending on specific requirements, leads to rapidly increasing new applications of nanoparticles and nanomaterials [2]. Nanotechnology is an extremely efficacious technology and useful to design and development of several sorts of novel products with its potential medical applications on early disease detection, treatment, and prevention [3]. Nanotechnology involves the design, manipulation, production, and application of materials in the nanometer range 10^{-9} m [4]. Biological characteristics of NPs depend on its interaction with proteins, membranes, cells, DNA, and organelles and building a series of nanoparticle-biological interfaces attach with colloidal forces in addition to biophysicochemical interactions [5]. This leads to the formation of protein coronas, particle wrapping,

intracellular uptake, and biocatalytic processes that could have biocompatible or bio-adverse outcomes. Among all the nanoparticles developed and characterized, silver nanoparticle occupy significant position due to their several characterized that involve chemical stability, favorable electrical conductivity, and catalytic activity [6]. As a result it is commonly used in number of medical preparations acting as an antimicrobial against pathogens [7].

There are a variety of preparation techniques have been reported for the synthesis of nanoparticles include physical, chemical and biological. Among these techniques, biosynthesis of metal nanoparticles is of particular interest because of its benign advantages compared to the other processes, which including environmentally friendly, cheap cost, safe and rapid [8,9].

Candida species are ascomycetes belonging to the group of hemiascomycetes. *Candida* spp are part of the normal human microbiota, usually found in the genitourinary tracts, gastrointestinal, the oral cavity and to a lesser extent on the skin of most healthy humans [10,11]. The normally pose no threat but under certain circumstances, when patients are

immunocompromised, candida can become a pathogen [12]. While the incidence of Candida infections is increasing, the choice of suitable antifungal agents is limited due to the resistance of some species to several antifungals. Candida species can cause superficial to life-threatening candidemia and hospital-acquired infections in humans [13].

Rhubarb is considered from medical plants because it contains a mixture of medicinal compounds such as tannins, glycosides, flavonoids, anthraquinone, volatile oils, and saponins that are biologically active compounds used in medicine due to their efficiency as antibacterial, antifungal, antioxidant, anticancer, wounds healing and immune-enhancing activity [14]. Numerous experimental and clinical studies have been performed related to the effects of medicinal plants in order to reduce the rates of diseases and treated all over the world [15,16].

Materials and Methods

Fungal strains

The Candida species isolates were collected and selected from many different clinical specimens at Al-Ramadi Teaching Hospital, where collected fourteen isolates revert to different species. The four Candida species isolates were identified based on their morphology also the Vitek 2 system was performed to identify the species and confirmation its diagnosis.

Preparation of plant extract

The fresh plants were collected from local markets then identified by a plant taxonomist in Salahuddin University Herbarium as *Rheum ribes* L. After that fresh plants washed many times with tap water and with distilled water to remove dust and soil particles from their surfaces. Weights 40 gm of fresh plant, then chopped to small pieces and maceration in 160 ml sterile distilled water for 24h as shown in scheme (1), then filtered with Whatman No.1 filter paper. Filtrate solution was collected with good storage and airtight at refrigerator temperature for further analysis [17].


Preparation of Nanoparticles

Nanoparticles (AgNPs) were prepared by the green synthesis method using plant extract of *Rheum ribes*, where 10 ml of plant extract was added to 90 ml of AgNO_3 solution at concentration 1mM as shown in scheme 1. After that, the combined solution were motivated dynamically at temperatures 25°C ; pH 9; and concentrations of 1 mM, with observing the gradual change in color of the solution [18].

Antifungal activity of nanoparticles test

Agar well diffusion method used to test the activity of nanoparticles as antifungal, where spread the suspension on sabouraud dextrose agar after compared with Macfarland tube (0.5) by cotton swab then made wells in each plate with diameter 6mm by cork borer, poured in each them 75 μl of nanoparticles solution and incubated overnight at 37°C . After that, the inhibition zones surrounded

wells were measured by Vernier caliper with millimeter-scale [19].

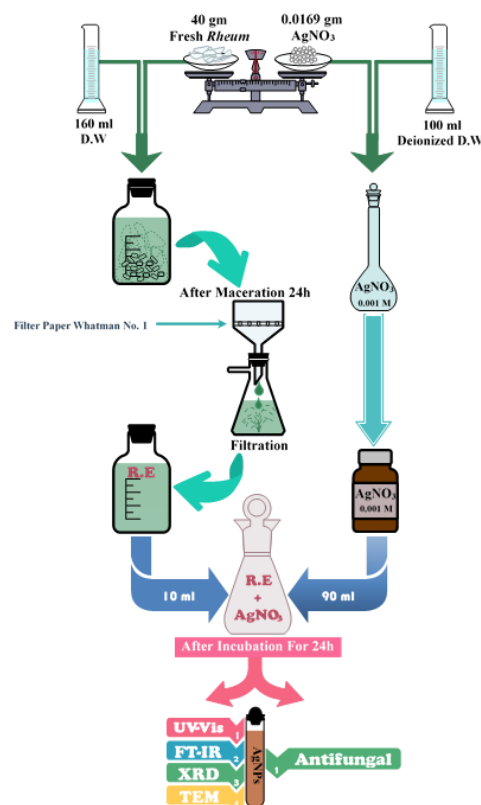

Scheme 1: Scheme explain Preparation procedure of Plant Extract, Metal Salts and Synthesis of Nanoparticles.

Results and Discussion

Identification of fungal strains

The Candida species isolates which collected show revert to different species and It has been identified four species which includes *Candida albicans*, *Candida tropicalis*, *Candida krusei*, and *Candida glabrata* figure (1) based on their morphology also the Vitek 2 system was performed to identify the species and It has been confirmed diagnosis at the species level (appendix a).

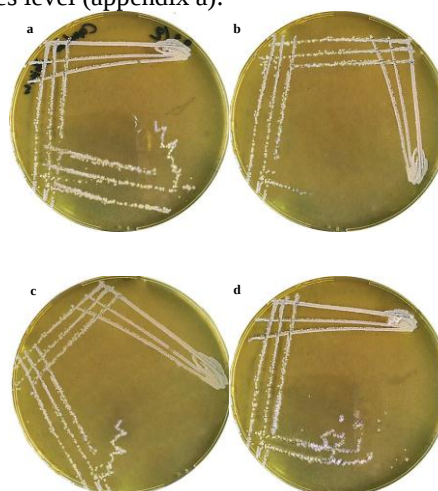


Fig.1: Candida spp. on SDA a) *Candida albicans*, b) *Candida glabrata*, c) *Candida tropicalis*, d) *Candida krusei*.

Green synthesis and characterization of AgNPs

Nanoparticles were prepared by using the green synthesis method by adding plant extract to the aqueous solution of AgNO_3 , where the synthesis of the nanoparticles was confirmed using plant extract of *Rheum ribes* by change the colorless solution to brown-yellowish color figure (2), this indicates the formation of silver nanoparticles. Also formation and characterization of AgNPs were determined by many techniques, the ultraviolet-visible spectroscopy (UV-

1800, Shimadzu) employed to identify nanoparticles absorption within the range (300-600) where figure (2) explain the UV-Vis spectrum of biosynthesized nanoparticles by using plant *Rheum* extract. Were the absorption peak was at the wavelength (425) nm, and it turns out this absorbance peak prove the formation of metallic silver nanoparticles located in the surface plasmon resonance of silver nanoparticles region [20].

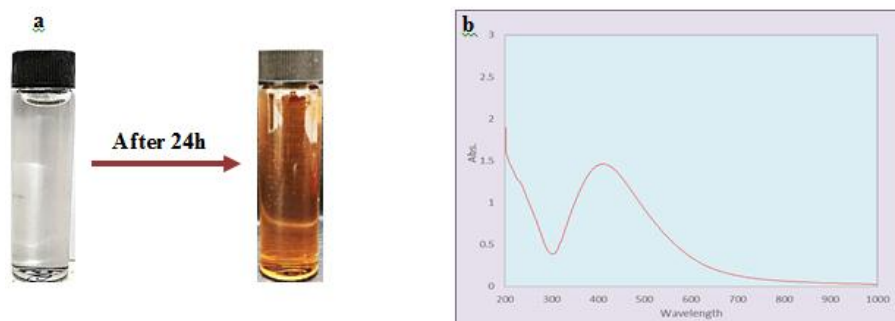


Fig.2: a) Explain color observation of AgNPs, b) UV-Vis spectrum of AgNPs synthesized.

The figure (3) show the results of the Fourier transform infrared spectroscopy (FTIR-600, Biotech) for treatment that used *Rheum* extract in preparation of silver nanoparticles. There are several peaks noticed in the figures shown below, some of them appear broad and strong peaks in the wavenumbers ($3421\text{--}3213\text{ cm}^{-1}$) assigned to O - H stretching vibration in alcohol and carboxyl acid. While the active group C=C stretching vibration that found in the aromatic and amides compounds showed strong and sharp peaks at ($1628\text{--}1593\text{ cm}^{-1}$), on the other side, the bond S=O stretching vibration appeared as very sharp and strong peaks at the wavenumbers that ranged from 1390 cm^{-1} to 1361 cm^{-1} . As well as the medium and broad peaks at wavenumbers ($1113\text{--}1034\text{ cm}^{-1}$) are mainly due to C-N stretching vibration in amines. The bond in the region between 829 cm^{-1} and 777 cm^{-1} is attributed to the presence of active group of amines (N-H stretching vibration) in samples. The absorption bands at ($526\text{--}501\text{ cm}^{-1}$) appeared as weak peaks that indicated to the bond S-S Disulfide stretching vibration that agree with Balakumaran [21].

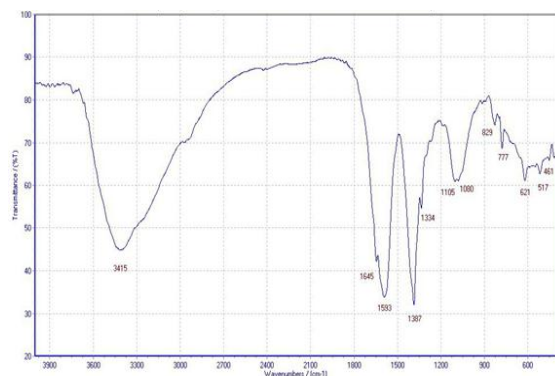


Fig.3: FT-IR Spectrum of AgNPs synthesized.

The figure 4 exhibit X-Ray diffraction (XRD-6000, Shimadzu) with 2 theta angles that ranged from $20\text{--}80^\circ$; this patterns was similar to the Bragg's reflection of silver nanocrystal, which may be index to the (111), (200), (220), (311) when compared with cards of the Joint Committee on Powder Diffraction Standards (JCPDS). The crystal structure nature of the synthesized silver nanoparticles is face center cube (FCC) that agreement with results of previous studies [22,23].

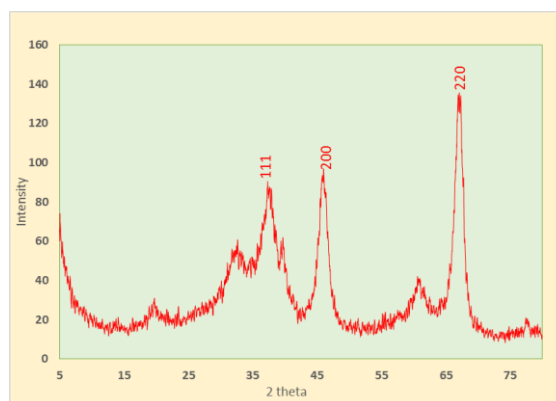


Fig.4: XRD pattern of AgNPs synthesized.

The TEM (Phillips CM10) analysis of silver nanoparticles synthesized by using the *Rheum* extract plant as a reducing agent proved that shape was spherical with different sizes. Figures (5) show the particle sizes and shapes of the treatment groups. Where noticed the particle size in range (5-30) nm. these data correspond with Tawfeeq *et al.* and Muthuraman *et al.* [24,25].

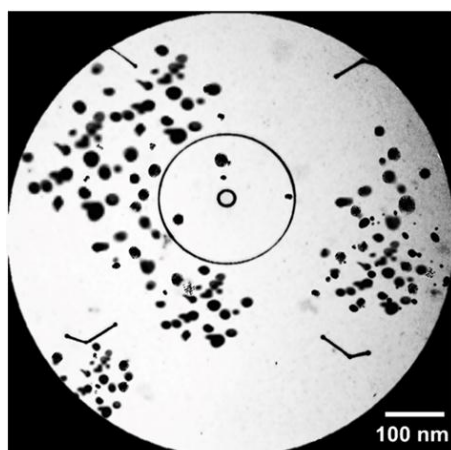


Fig. 5: TEM image of AgNPs synthesized using *Rheum ribes* extract.

Antifungal activity

In this study, silver nanoparticles were successfully synthesized by the biological method using plant extract of *Rheum* as reduce agent as shown in the procedure mentioned in the scheme (1). AgNPs exhibited antimicrobial activity against pathogenic microorganisms with varying degrees, which may be due to their higher surface activity, as submitted by the diameters of the inhibition zone, that agree with what obtained by Hamidi *et al.*, and Maeah [26,27]. Where nanoparticles showed a good antifungal activity against *Candida tropicalis* greater than other species then it followed by *Candida krusei*, after that *Candida albicans*, and *Candida glabrata* came last as shown in table (1). One of the possible modes of action of the plant mediated silver nanoparticles might be to attach to the cell surface and disrupt the cell membrane and interact. After penetration, Ag NPs release silver ions which interacted with DNA, proteins and sulfur containing cell constituents, therefore, the organisms were prevented.

Table1: Explain Antifungal activity of silver nanoparticles.

Microorganisms	Inhibition Zone (mm)	
<i>Candida albicans</i>	17	
<i>Candida krusei</i>	18	
<i>Candida tropicalis</i>	19	
<i>Candida glabrata</i>	17	

Conclusion

The method of green synthesis of nanoparticles by plant extract proved its competence in the synthesis of silver nanoparticles. Also, silver nanoparticles that were obtained showed antimicrobial effects against yeast and thus it can be investigated for further medicinal applications where the efficiency of nanoparticles against *Candida tropicalis* greater than other species, then it followed by *Candida krusei*, after that *Candida albicans*, and *Candida glabrata* came last.

bioMérieux Customer: Laboratory Report		Printed Oct 15, 2019 00:05 CDT																																													
System #:		Autoprint																																													
Patient Name: MMA 2		Patient ID: 1775																																													
Isolate: 1775 (To be reviewed)																																															
Card Type: YST Bar Code: 2430834403310985 Testing Instrument: 000014EED3FH (MedLab)																																															
Setup Technologist: Laboratory Administrator(LabAdmin)																																															
Biomnumber: 4502544065327951																																															
Organism Quantity: Selected Organism: <i>Candida albicans</i>																																															
Comments:																																															
<table border="1"> <tr> <td>Identification Information</td> <td>Card: YST</td> <td>Lot Number: 2430434403</td> <td>Expires: Mar 9, 2020 13:00 CDT</td> </tr> <tr> <td>Completed:</td> <td>Oct 14, 2019 13:00 CDT</td> <td>Status: Final</td> <td>Analysis Time: 18:00 hours</td> </tr> <tr> <td>Organism Origin</td> <td colspan="3">VITEK 2</td> </tr> <tr> <td>Selected Organism</td> <td colspan="3">97% Probability <i>Candida albicans</i></td> </tr> <tr> <td>Biomnumber:</td> <td colspan="3">4502544065327951</td> </tr> <tr> <td>Confidence:</td> <td colspan="3">Excellent identification</td> </tr> <tr> <td colspan="4">SRF Organism</td> </tr> <tr> <td colspan="4">Analysis Organisms and Tests to Separate:</td> </tr> <tr> <td colspan="4">Analysis Messages:</td> </tr> <tr> <td colspan="4">See product information for additional information.</td> </tr> <tr> <td colspan="4">Analysis Contradicting Typical Biopattern(s)</td> </tr> </table>				Identification Information	Card: YST	Lot Number: 2430434403	Expires: Mar 9, 2020 13:00 CDT	Completed:	Oct 14, 2019 13:00 CDT	Status: Final	Analysis Time: 18:00 hours	Organism Origin	VITEK 2			Selected Organism	97% Probability <i>Candida albicans</i>			Biomnumber:	4502544065327951			Confidence:	Excellent identification			SRF Organism				Analysis Organisms and Tests to Separate:				Analysis Messages:				See product information for additional information.				Analysis Contradicting Typical Biopattern(s)			
Identification Information	Card: YST	Lot Number: 2430434403	Expires: Mar 9, 2020 13:00 CDT																																												
Completed:	Oct 14, 2019 13:00 CDT	Status: Final	Analysis Time: 18:00 hours																																												
Organism Origin	VITEK 2																																														
Selected Organism	97% Probability <i>Candida albicans</i>																																														
Biomnumber:	4502544065327951																																														
Confidence:	Excellent identification																																														
SRF Organism																																															
Analysis Organisms and Tests to Separate:																																															
Analysis Messages:																																															
See product information for additional information.																																															
Analysis Contradicting Typical Biopattern(s)																																															
Installed VITEK 2 Systems Version: 08.01 MIC Interpretation Guideline: Global CLSI-based AES Parameter Set Name: Global CLSI-based+Phenotypic																																															
Page 1 of 1																																															

bioMérieux Customer: Laboratory Report		Printed Oct 15, 2019 10:18 CDT																																									
System #:		Autoprint																																									
Patient Name: MMA 16		Patient ID: 1790																																									
Isolate: 1790 (To be reviewed)																																											
Card Type: YST Bar Code: 2421091403207878 Testing Instrument: 000014EED3FH (MedLab)																																											
Setup Technologist: Laboratory Administrator(LabAdmin)																																											
Biomnumber: 6502043066326551																																											
Organism Quantity: Selected Organism: <i>Candida tropicalis</i>																																											
Comments:																																											
<table border="1"> <tr> <td>Identification Information</td> <td>Card: YST</td> <td>Lot Number: 2431067403</td> <td>Expires: Mar 9, 2020 13:00 CDT</td> </tr> <tr> <td>Completed:</td> <td>Oct 14, 2019 17:20 CDT</td> <td>Status: Final</td> <td>Analysis Time: 17:77 hours</td> </tr> <tr> <td>Organism Origin</td> <td colspan="3">VITEK 2</td> </tr> <tr> <td>Selected Organism</td> <td colspan="3">93% Probability <i>Candida tropicalis</i></td> </tr> <tr> <td>Biomnumber:</td> <td colspan="3">6502043066326551</td> </tr> <tr> <td>Confidence:</td> <td colspan="3">Very good identification</td> </tr> <tr> <td colspan="4">SRF Organism</td> </tr> <tr> <td colspan="4">Analysis Organisms and Tests to Separate:</td> </tr> <tr> <td colspan="4">Analysis Messages:</td> </tr> <tr> <td colspan="4">Analysis Contradicting Typical Biopattern(s)</td> </tr> </table>				Identification Information	Card: YST	Lot Number: 2431067403	Expires: Mar 9, 2020 13:00 CDT	Completed:	Oct 14, 2019 17:20 CDT	Status: Final	Analysis Time: 17:77 hours	Organism Origin	VITEK 2			Selected Organism	93% Probability <i>Candida tropicalis</i>			Biomnumber:	6502043066326551			Confidence:	Very good identification			SRF Organism				Analysis Organisms and Tests to Separate:				Analysis Messages:				Analysis Contradicting Typical Biopattern(s)			
Identification Information	Card: YST	Lot Number: 2431067403	Expires: Mar 9, 2020 13:00 CDT																																								
Completed:	Oct 14, 2019 17:20 CDT	Status: Final	Analysis Time: 17:77 hours																																								
Organism Origin	VITEK 2																																										
Selected Organism	93% Probability <i>Candida tropicalis</i>																																										
Biomnumber:	6502043066326551																																										
Confidence:	Very good identification																																										
SRF Organism																																											
Analysis Organisms and Tests to Separate:																																											
Analysis Messages:																																											
Analysis Contradicting Typical Biopattern(s)																																											
Installed VITEK 2 Systems Version: 08.01 MIC Interpretation Guideline: Global CLSI-based AES Parameter Set Name: Global CLSI-based+Phenotypic																																											
Page 1 of 1																																											

bioMérieux Customer: Laboratory Report		Printed Oct 15, 2019 10:05 CDT																																									
System #:		Autoprint																																									
Patient Name: MMA 12		Patient ID: 1786																																									
Isolate: 1786 (To be reviewed)																																											
Card Type: YST Bar Code: 2421091403207887 Testing Instrument: 000014EED3FH (MedLab)																																											
Setup Technologist: Laboratory Administrator(LabAdmin)																																											
Biomnumber: 6400104020005150																																											
Organism Quantity: Selected Organism: <i>Candida krusei</i>																																											
Comments:																																											
<table border="1"> <tr> <td>Identification Information</td> <td>Card: YST</td> <td>Lot Number: 2431067403</td> <td>Expires: Mar 9, 2020 13:00 CDT</td> </tr> <tr> <td>Completed:</td> <td>Oct 14, 2019 20:26 CDT</td> <td>Status: Final</td> <td>Analysis Time: 17:78 hours</td> </tr> <tr> <td>Organism Origin</td> <td colspan="3">VITEK 2</td> </tr> <tr> <td>Selected Organism</td> <td colspan="3">97% Probability <i>Candida krusei</i></td> </tr> <tr> <td>Biomnumber:</td> <td colspan="3">6400104020005150</td> </tr> <tr> <td>Confidence:</td> <td colspan="3">Excellent identification</td> </tr> <tr> <td colspan="4">SRF Organism</td> </tr> <tr> <td colspan="4">Analysis Organisms and Tests to Separate:</td> </tr> <tr> <td colspan="4">Analysis Messages:</td> </tr> <tr> <td colspan="4">Analysis Contradicting Typical Biopattern(s)</td> </tr> </table>				Identification Information	Card: YST	Lot Number: 2431067403	Expires: Mar 9, 2020 13:00 CDT	Completed:	Oct 14, 2019 20:26 CDT	Status: Final	Analysis Time: 17:78 hours	Organism Origin	VITEK 2			Selected Organism	97% Probability <i>Candida krusei</i>			Biomnumber:	6400104020005150			Confidence:	Excellent identification			SRF Organism				Analysis Organisms and Tests to Separate:				Analysis Messages:				Analysis Contradicting Typical Biopattern(s)			
Identification Information	Card: YST	Lot Number: 2431067403	Expires: Mar 9, 2020 13:00 CDT																																								
Completed:	Oct 14, 2019 20:26 CDT	Status: Final	Analysis Time: 17:78 hours																																								
Organism Origin	VITEK 2																																										
Selected Organism	97% Probability <i>Candida krusei</i>																																										
Biomnumber:	6400104020005150																																										
Confidence:	Excellent identification																																										
SRF Organism																																											
Analysis Organisms and Tests to Separate:																																											
Analysis Messages:																																											
Analysis Contradicting Typical Biopattern(s)																																											
Installed VITEK 2 Systems Version: 08.01 MIC Interpretation Guideline: Global CLSI-based AES Parameter Set Name: Global CLSI-based+Phenotypic																																											
Page 1 of 1																																											

bioMérieux Customer: Laboratory Report		Printed Oct 15, 2019 10:15 CDT																																									
System #:		Autoprint																																									
Patient Name: MMA 13		Patient ID: 1787																																									
Isolate: 1787 (To be reviewed)																																											
Card Type: YST Bar Code: 2421091403207889 Testing Instrument: 000014EED3FH (MedLab)																																											
Setup Technologist: Laboratory Administrator(LabAdmin)																																											
Biomnumber: 6000144024211211																																											
Organism Quantity: Selected Organism: <i>Candida glabrata</i>																																											
Comments:																																											
<table border="1"> <tr> <td>Identification Information</td> <td>Card: YST</td> <td>Lot Number: 2431067403</td> <td>Expires: Mar 9, 2020 13:00 CDT</td> </tr> <tr> <td>Completed:</td> <td>Oct 14, 2019 20:20 CDT</td> <td>Status: Final</td> <td>Analysis Time: 17:77 hours</td> </tr> <tr> <td>Organism Origin</td> <td colspan="3">VITEK 2</td> </tr> <tr> <td>Selected Organism</td> <td colspan="3">98% Probability <i>Candida glabrata</i></td> </tr> <tr> <td>Biomnumber:</td> <td colspan="3">6000144024211211</td> </tr> <tr> <td>Confidence:</td> <td colspan="3">Excellent identification</td> </tr> <tr> <td colspan="4">SRF Organism</td> </tr> <tr> <td colspan="4">Analysis Organisms and Tests to Separate:</td> </tr> <tr> <td colspan="4">Analysis Messages:</td> </tr> <tr> <td colspan="4">Analysis Contradicting Typical Biopattern(s)</td> </tr> </table>				Identification Information	Card: YST	Lot Number: 2431067403	Expires: Mar 9, 2020 13:00 CDT	Completed:	Oct 14, 2019 20:20 CDT	Status: Final	Analysis Time: 17:77 hours	Organism Origin	VITEK 2			Selected Organism	98% Probability <i>Candida glabrata</i>			Biomnumber:	6000144024211211			Confidence:	Excellent identification			SRF Organism				Analysis Organisms and Tests to Separate:				Analysis Messages:				Analysis Contradicting Typical Biopattern(s)			
Identification Information	Card: YST	Lot Number: 2431067403	Expires: Mar 9, 2020 13:00 CDT																																								
Completed:	Oct 14, 2019 20:20 CDT	Status: Final	Analysis Time: 17:77 hours																																								
Organism Origin	VITEK 2																																										
Selected Organism	98% Probability <i>Candida glabrata</i>																																										
Biomnumber:	6000144024211211																																										
Confidence:	Excellent identification																																										
SRF Organism																																											
Analysis Organisms and Tests to Separate:																																											
Analysis Messages:																																											
Analysis Contradicting Typical Biopattern(s)																																											
Installed VITEK 2 Systems Version: 08.01 MIC Interpretation Guideline: Global CLSI-based AES Parameter Set Name: Global CLSI-based+Phenotypic																																											
Page 1 of 1																																											

Appendix a: Reports of VITEK 2 System test

References

- [1] Varanda LC, Souza CGS, Moraes DA, Neves HR, Souza Junior JB, Silva MF, et al. (2019). Size and shape-controlled nanomaterials based on modified polyol and thermal decomposition approaches. A brief review. *Anais da Academia Brasileira de Ciencias*. **91**:1–32 p.
- [2] Naganathan K, Thirunavukkarasu S. (2017).

Green way genesis of silver nanoparticles using multiple fruit peels waste and its antimicrobial, anti-oxidant and anti-tumor cell line studies. IOP Conference Series: *Materials Science and Engineering*. **191**(1).

- [3] Das G, Patra JK, Debnath T, Ansari A, Shin HS. (2019). Investigation of antioxidant, antibacterial,

- antidiabetic, and cytotoxicity potential of silver nanoparticles synthesized using the outer peel extract of *Ananas comosus* (L.). *PLOS ONE*. **14**(8):1–19.
- [4] Saliem AH, Ibrahim OMS, Ibrahim S. (2016). Biosynthesis of Silver Nanoparticles using *Cinnamom zeylanicum* Plants Bark Extract. *Kufa Journal of veterinarian medical science*. **(7)**.
- [5] Neagu M, Piperigkou Z, Karamanou K, Engin AB, Docea AO, Constantin C, et al. (2017). Protein bio-corona: critical issue in immune nanotoxicology. *Archives of Toxicology*. **91**(3):1031–48.
- [6] Ahmed S, Saifullah, Ahmad M, Swami BL, Ikram S. (2016). Green synthesis of silver nanoparticles using *Azadirachta indica* aqueous leaf extract. *Journal of Radiation Research and Applied Sciences*. **9**(1):1–7.
- [7] Chung IM, Park I, Seung-Hyun K, Thiruvengadam M, Rajakumar G. (2016). Plant-Mediated Synthesis of Silver Nanoparticles: Their Characteristic Properties and Therapeutic Applications. *Nanoscale Research Letters*. **11**(1):1–14.
- [8] Murali Krishna I, Bhagavanth Reddy G, Veerabhadram G, Madhusudhan A. (2016). Eco-friendly green synthesis of silver nanoparticles using *salmalia malabarica*: synthesis, characterization, antimicrobial, and catalytic activity studies. *Applied Nanoscience (Switzerland)*. **6**(5):681–9.
- [9] Ajitha B, Ashok Kumar Reddy Y, Sreedhara Reddy P. (2014). Biosynthesis of silver nanoparticles using *Plectranthus amboinicus* leaf extract and its antimicrobial activity. *Spectrochimica Acta - Part A: Molecular and Biomolecular Spectroscopy*. **128**:257–62.
- [10] Badiie P, Badali H, Boekhout T, Diba K, Moghadam AG, Hossaini Nasab A, et al. (2017). Antifungal susceptibility testing of *Candida* species isolated from the immunocompromised patients admitted to ten university hospitals in Iran: Comparison of colonizing and infecting isolates. *BMC Infectious Diseases*. **17**(1):1–8.
- [11] Devi L, Maheshwari M. (2014). Speciation of *Candida* Species Isolated From Clinical Specimens by Using Chrom Agar and Conventional Methods. *International Journal of Scientific and Research Publications*. **4**(3):1–2.
- [12] Mba IE, Nweze EI. (2020). The use of nanoparticles as alternative therapeutic agents against *Candida* infections: an up-to-date overview and future perspectives. *World Journal of Microbiology and Biotechnology*. **36**(11).
- [13] Mahmoudabadi AZ, Rezaei-Matehkolaei A, Ghanavati F. (2015). The susceptibility patterns of *Candida* species isolated from urine samples to posaconazole and caspofungin. *Jundishapur Journal of Microbiology*. **8**(3):0–4.
- [14] Naemi F, Asghari G, Yousofi H, Yousefi HA. (2014). Chemical composition of essential oil and anti-trichomonas activity of leaf, stem, and flower of *Rheum ribes* L. extracts. *Avicenna journal of phytomedicine*. **4**(3):191–9.
- [15] Kooti W, Farokhipour M, Asadzadeh Z, Ashtary-Larky D, Asadi-Samani M. (2016). The role of medicinal plants in the treatment of diabetes: a systematic review. *Electronic physician*. **8**(1):1832–42.
- [16] Shedoeva A, Leavesley D, Upton Z, Fan C. (2019). Wound healing and the use of medicinal plants. Evidence-based Complementary and Alternative Medicine. **30**.
- [17] Yeshiwas D, Mekonnen A. (2018). Comparative study of the antioxidant and antibacterial activities of two guava (*Psidium guajava*) fruit varieties cultivated in Andasa Horticulture Site, Ethiopia. *Chemistry International*. **4**(3):154–62.
- [18] Kumar PR, Jeba DP, David SA, Chinnasamy M. (2019). Phytochemical And Antimicrobial Studies Of Biosynthesized Silver Nanoparticles Using *Anacardium Occidentale* Fruit Extract. *INTERNATIONAL JOURNAL OF RESEARCH AND ANALYTICAL REVIEWS (IJRAR)*. **6**(1):985–94.
- [19] Shivananda CS, Asha S, Madhukumar R, Satish S, Narayana B, Byrappa K, et al. (2016). Biosynthesis of colloidal silver nanoparticles: Their characterization and potential antibacterial activity. *Macromolecular Research*. **24**(8):684–90.
- [20] Al-Ogaidi IAZ. (2017). Detecting the antibacterial activity of green synthesized silver (Ag) nanoparticles functionalized with ampicillin (Amp). *Baghdad Science Journal*. **14**(1):117–25.
- [21] Balakumaran MD, Ramachandran R, Balashanmugam P, Mukeshkumar DJ, Kalaichelvan PT. (2016). Mycosynthesis of silver and gold nanoparticles: Optimization, characterization and antimicrobial activity against human pathogens. *Microbiological Research*. **182**:8–20.
- [22] Satpathy S, Patra A, Ahirwar B, Delwar Hussain M. (2018). Antioxidant and anticancer activities of green synthesized silver nanoparticles using aqueous extract of tubers of *Pueraria tuberosa*. *Artificial Cells, Nanomedicine and Biotechnology*. **46**(sup3):71–85.
- [23] Shankar PD, Shobana S, Karuppusamy I, Pugazhendhi A, Ramkumar VS, Arvindnarayan S, et al. (2016). A review on the biosynthesis of metallic nanoparticles (gold and silver) using bio-components of microalgae: Formation mechanism and applications. *Enzyme and Microbial Technology*. **95**:28–44.
- [24] Tawfeeq SM, Maaroo MN, Al-ogaidi I. (2017). Synergistic effect of biosynthesized silver nanoparticles with antibiotics against multi-drug resistance bacteria isolated from children with diarrhoea under five years. *Iraqi Journal of Science*. **58**(1).
- [25] Muthuraman MS, Nithya S, Vinoth kumar V, Christena LR, Vadivel V, Subramanian NS, et al. (2019). Green synthesis of silver nanoparticles using *Nardostachys jatamansi* and evaluation of its anti-biofilm effect against classical colonizers. *Microbial Pathogenesis*. **126**:1–5.

[26] Hamidi A, Taghavizadeh Yazdi ME, Amiri MS, Hosseini HA, Darroudi M. (2019). Biological synthesis of silver nanoparticles in *Tribulus terrestris* L. extract and evaluation of their photocatalyst, antibacterial, and cytotoxicity effects. *Research on*

Chemical Intermediates. **45(5)**:2915–25.

[27] Maeah R kwater. (2018). Biosynthesis of Silver Nanoparticles Using *Eucalyptus Bicolor* Bark and their Antimicrobial Activity. *Diyala Journal For Pure Science*. **14(1)**:190–202.

التوليف الأخضر لجسيمات الفضة النانوية باستخدام مستخلص الريواز وتقييم فعاليتها كمضاد فطري ضد بعض انواع المبيضات

مصطفى مهدي عودة ، هاجر علي شريف ، بري لطيف محمد

قسم علوم الحياة ، كلية العلوم ، جامعة كركوك ، كركوك ، العراق

الملخص

يعتبر تركيب الجسيمات النانوية بالطريقة الخضراء باستخدام المستخلصات النباتية وتطبيقها في الطب الحيوي مجالاً بحثياً مزدهراً. لذلك، في هذه الدراسة، تم استخدام نبات الريواز كعامل مختزل في تخليق جسيمات الفضة النانوية واختبار فعاليتها كمضاد فطري. حيث تم تشخيص جسيمات الفضة النانوية باستخدام عدة تقنيات مثل التحليل الطيفي للأشعة فوق البنفسجية UV-Vis، وحيود الأشعة السينية XRD، والتحليل الطيفي بالأشعة تحت الحمراء FTIR، والمجهر الإلكتروني النافذ TEM. حيث أظهرت نتيجة الفحص بالأشعة فوق البنفسجية UV-Vis قمة امتصاص لجسيمات الفضة النانوية عند الطول الموجي (425) نانومتر، وأكد اختبار XRD وجود جسيمات الفضة النانوية بوضوح من خلال مقارنة القيم الناتجة مع بطاقات JCPDS. بينما كشف التحليل الطيفي FTIR عن وجود مجاميع الفعالة للاسترات الأمينية والألفاينية، التي تشارك في اختزال واستقرار الجسيمات النانوية AgNPs. وظهرت الصورة المجهرية TEM لجسيمات الفضة النانوية أنها كروية الشكل وبحجم يتراوح بين 5-45 نانومتر. من خلال ملاحظة مناطق التثبيط أظهرت جسيمات الفضة النانوية المُصنَّعة نشاطاً مضاداً جيداً للفطريات ضد بعض انواع المبيضات.