IASJ المجلات الاكاديمية العراقية

Tikrit Journal of Pure Science

ISSN: 1813 – 1662 (Print) --- E-ISSN: 2415 – 1726 (Online)

Journal Homepage: http://tjps.tu.edu.iq/index.php/j

Growth, structural and magnetic properties of Gadolinium oxide (Gd_2O_3) thin films

Huda Saadi Ali1, N. K. Hassan1

Department of Physics , College of Education for Pure Sciences , Tikrit University , Tikrit , Iraq

DOI: http://dx.doi.org/10.25130/tjps.25.2020.094

ARTICLE INFO.

Article history:

-Received: 4 / 3 / 2020

-Accepted: 30 / 5 / 2020

-Available online: / / 2020

Keywords: Gd_2O_3 , XRD , VSM , p-type, saturation magnetization (Ms).

Corresponding Author:

Name: Huda Saadi Ali1

E-mail: wwhdgs@yahoo.com

Tel:

ABSTRACT

Gd_{2O3} nanoparticles thin films obtain through the spin coating techniques deposited on substrate of p-Si(100) . The structural properties of the thin film were measured by X-ray diffraction technology (XRD) to know the crystal structure and the effect of the difference of different annealing temperatures on the crystal growth of these samples, and the scanning electron microscopy examinations (SEM) and the magnetic properties were studied using the Vibrating Sample Magnetometer(VSM) of Various annealing temperatures (500,600,700,800)℃. The results of the X-ray diffraction showed that all the prepared membranes have a multi-crystalline structure with different diffraction values and directions and the Gd_2O_3 thin film were of the cubic type and it was noted that by increasing the annealing temperature we get the best crystalline development and the results of SEM showed that the shape of the deposited nanoparticles was spherical, and we note an increase in the saturation magnetization (MS) about (0.1421 - 0.1811) emu / g with increased of annealing temperature.

1- Introduction

Rare earth elements are a group of seventeen chemical elements in the periodic table. After discovering its composition the same sediments that the lanthanides form and have similar chemical properties arising from their 4f electron. The oxides of the lanthanides group (Ln_2O_3) are very thermally stable, they are at high temperatures and are characterized by their extreme heat resistance[1-5].Gadolinium atomic number 64 and is a white, silver metal of a group of rare earth elements. Gadolinium oxide (Gd_2O_3) is that has chemical strength and thermal stability and low phonon energy [6]. In ambient conditions, these materials exist in three different polymorphic forms of A ,B, and C. The A phase has a hexagonal structure, the B phase has a monoclinic structure and the C phase has a cubic structure as With an increase in temperature ,phase transitions usually follow the sequence of C-B-A for most RE_2O_3 with medium-sized action's [7]. In addition reported the C-B and B-A phase transitions in Gd_2O_3 at the temperatures of about 1500K and 2443K,respectively [8]. The Gd^{3+} ion has a $^8S_{7/2}$ ground state, it carries the characteristics of ferromagnetic materials at room temperature[9,10]. The Curie point is 293 k (20 ° C, or 68 ° F). Above this temperature the material becomes a diamagnetic [11,12]. Spin coating processes of colloidal suspensions are carried out in four different stages, the first occurs quickly and the second takes a long time. In the first stage, colloidal liquid is deposited as a drop on a fixed substrate. In the second stage, the substrate is accelerated to a specific rotational speed and the liquid diffuses to form the film approximately. In the third stage, the liquid spreads out and softens, and is controlled by centrifugal force and viscous shear force. In the fourth stage, the film becomes delicate with the effect of fumigation, which reduces the thickness of the film. The transition from the third to the fourth stage depends on the properties of the liquid used in the coating. For colloidal suspension, the thickness of thin films can decrease during this fourth stage with the same particle size by the influence of capillary forces that affect the aggregation of the particles[13]. In this work, we prepared Gd_2O_3 nanoparticles by the sol-gel technique, then obtained thin films at different temperatures of spin coating technique and studied their structural and magnetic properties.

2- Method of Experimental

2-1 Sol-Gel Processing of Gd_2O_3

A simple relating to procedure is carried out to grow quality Gd_2O_3. During the first step mixing 0.283 g of

Gdd_2O_3 powder for 1 h 99.9% party with 40 ml of distilled water followed by drop wise addition of dilute HNO_3 until reach a clear. The pH of the mixture is then adjusted to 13.1 by adding drops of KOH solution with constant stirring for three horse finally sol is obtained. The chemical reaction steps and flow chart diagram of hydrothermally synthesized Gd_2O_3 are described by following equations and fig(1)respectively .

Acidification: $Gd_2O_3 + 6HNO_3 \rightarrow 2Gd(NO_3)_3 + 3\ H2O$ ---- **(2-1)**

Hydrolysis**:** $Gd(NO_3)_3 + 3\ kOH \rightarrow Gd(OH)_3 + 3\ kNO_3$ -----**(2-2)**

Dehydration**:** $2\ Gd(OH)_3 \rightarrow Gd_2O_3$ **(Nano powder)** $+ 3\ H_2O$ ----**(2-3)**

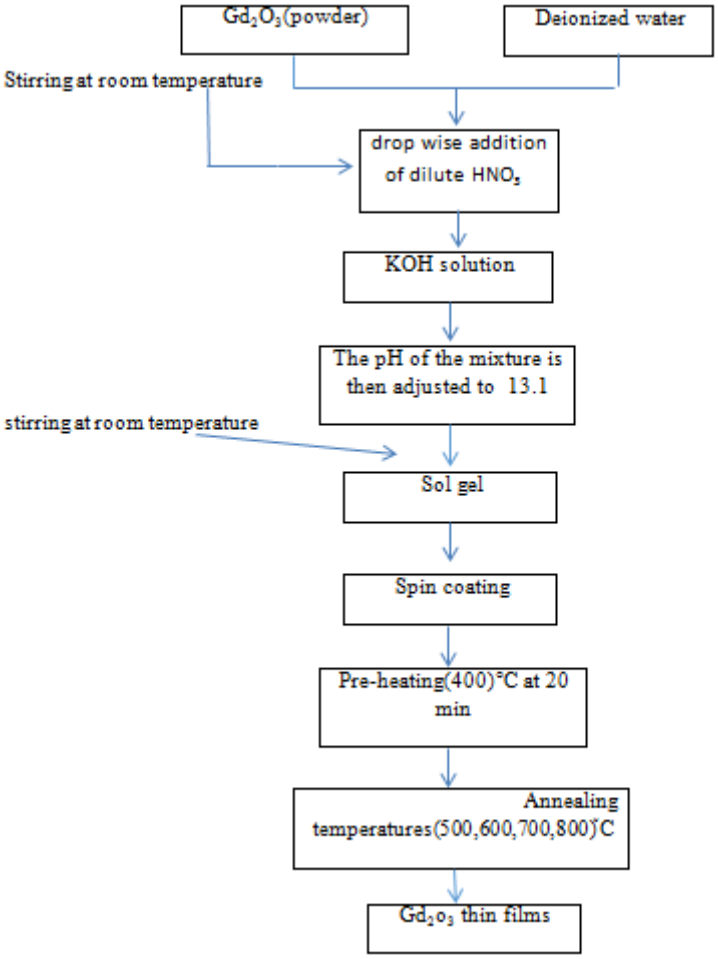

Fig.1: Chart showing preparation of the sol-gel and thin film deposition

2-2 Film deposition

The Gd_2O_3 nanomaterial was deposited on substrate of p- Si (100). Before deposition , substrate were cleaned with dilute HCL, acetone ,ethanol and distilled water. The films has deposited on substrate by spin coating at room temperature with rate of 3000 rpm for 30 s. After each coating the deposited films were dried at (400˚C)at (20 min) the coating and drying procedures were four times, all the films were annealed for 1h at(500,600, 700 and 800) ° C. The crystallographic information was revealed through x-ray diffraction type (SHIMADZU) that employs a Cu K_α source (λ=0.1543 nm).The crystallite size were calculate using Scherrer equation (1) [14]:

$Cs = h\ \lambda\ /\ \beta\ \cos\ \Theta$ ---------- (1)

Where Cs the crystallite size , h is the factor of microstructure (K =0.94), λ is the wavelength of radiation, β is the full-width at half-maximum (FWHM) and Θ is the diffraction angle. An examination VSM (CM120 Philips) was conducted to study the magnetic properties of samples prepared from Gd_2O_3 nanostructure. The saturation magnetization (*MS*) is essentially the limit value to which the curve tends within the high-field region, and is reached when all the magnetic moments in the material are aligned with the external field.

3- Results and Discussion

3-1 Structural Properties

the XRD patterns of Gd2O3 films fig (2) deposited on substrate p-Si (1 00) heat-treated at temperature

(500–800)C. For films annealed at higher temperature intense and typical diffraction peaks of cubic Gd_2O_3 with spatial group Ia3 (global card (00-012-0797))[15] appear. The crystallite size of Gd_2O_3 in films was estimated following the equation(1). Oriented growth of (431) face has been observed. When the annealing temperature was increased to 700℃, the films transformed from (2 2 2) orientation dominated to (4 0 0) orientation dominated. The transformation of orientation has been also observed in the electron diffraction patterns exhibit mainly rings associated to (2 2 2), (4 0 0), (4 4 0) and (6 2 2) planes of Gd_2O_3 cubic phase, which were already observed by XRD experiment on a multiplayer waveguide heat treated in the same conditions[16,17]. The annealing can induce the nucleation of small grains (defect free). If the annealing is long enough/high enough temperature continued growth of these new grains (defect free) may eventually become larger than the original grain size. So one can expect annealing to induce a grain size reduction (initially, incomplete recrystallization) and then an ultimately (possibly) larger grain size[18,19]. And the appearance of vertices indicates that the installation of samples deposited with different annealing temperature is a multi-crystalline structure because there is more than one peak . A small displacement of some peaks was also observed, and this may be due to mechanical stress [20].

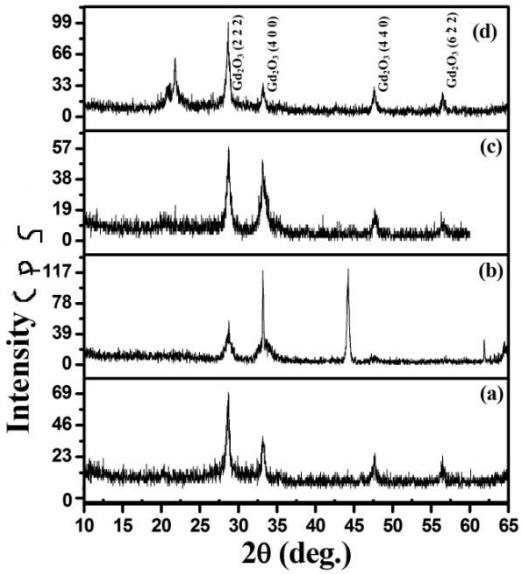

Fig 2: XRD patterns of the Gd2O3 thin films deposited on substrate of p- Si (100) a-(500℃),b- (600℃) , c-(700℃) and d-(800℃)

3-2 scanning electron microscopy (SEM)

The morphologies of Gd_2O_3 thin film annealed at different temperature (500,600,700,800)°C investigated in fig.(3), this figure confirms the existence of Gd_2O_3 nanoparticles and approximate spherical [21] and grain size of the particles investigated in fig.(3). Finely grain size of the particles was increased with increasing the annealing temperature.

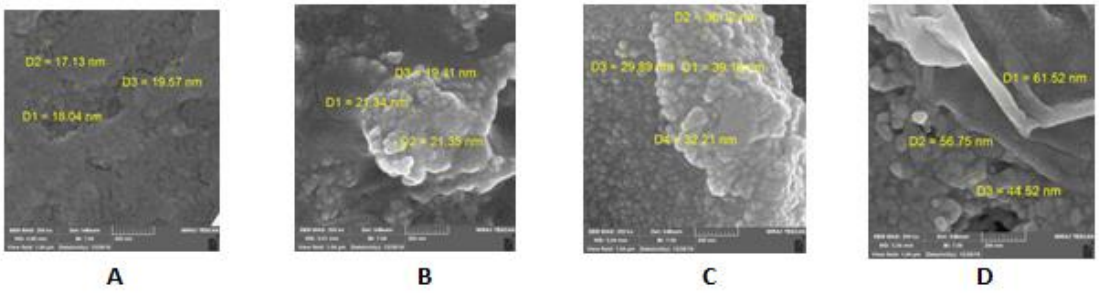

Fig. 3: SEM micrographs of Gd_20_3 thin films deposited on p-Si(100) substrate and annealing for 1h with different annealing temperatures: A (500 °C), B(600 °C) , C(700°C) , D (800°C)

3-3 Magnetic properties

The vibrating sample magnetometer (VSM) was used to study the Gd_2O_3 nanoparticles deposited on p-Si(100) substrate and annealing for 1h at different temperatures (500,600,700 and 800)°C. The hysteresis loops shown in fig.(4) the values of specific saturation magnetization (Ms) increased with increasing annealing temperature as shown in fig.(5). Can be explained the magnetic parameters (specific saturation magnetization (Ms)) as a function of heat treatment may be due to the growth of the grains with increasing annealing temperature. [22]

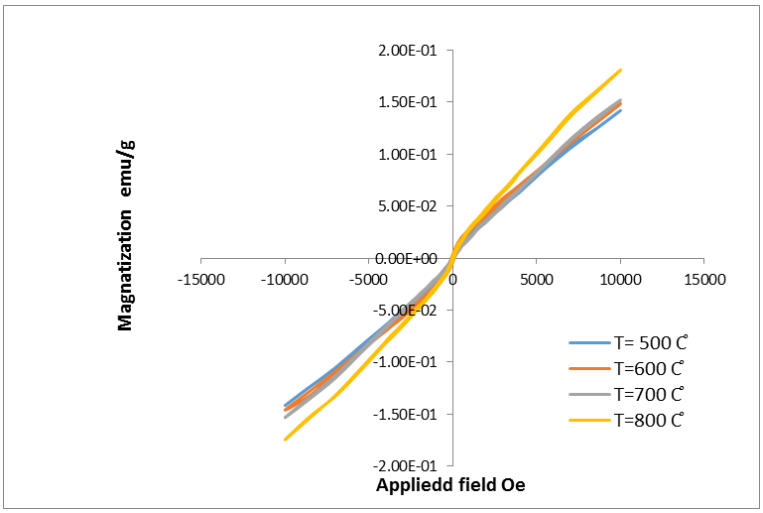

Fig. 4. Hysteresis loops of Gd_2O_3 nanoparticles obtained at different annealing temperatures

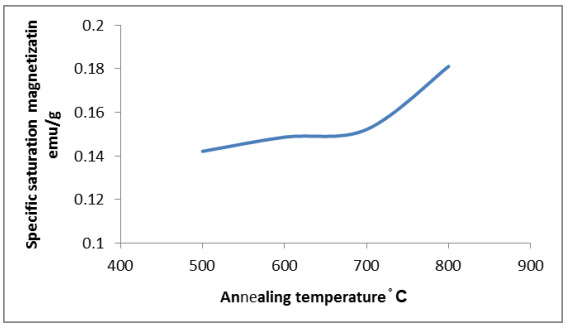

Fig 5 .The specific saturation magnetization of Gd_2O_3 for different annealing temperature

Conclusion

The crystalline development was greatly affected by the annealing temperatures.

The x-ray analysis for prepared Gd_2O_3 thin films shows that the structures are cube and the crystallite size increases with increasing the annealing temperature.

The scanning electron microscope(SEM) analyses of Gd_2O_3 nano-particle shows approximate spherical as well as the specific saturation magnetization (Ms) increased with increasing annealing temperature **.**

References

[1] Tian, Y.; He, Y. and Y. Zhu, (2004). Low temperature synthesis and characterization of molybdenum disulfide nanotubes and Nano rods, *Materials Chemistry and Physics*, **87(1)**: 87–90.

[2] Wu, G.; Zhang, L.; Cheng, B.; Xie, T. and Yuan, X. (2004). Synthesis of Eu_2O_3 nanotube arrays through a facile sol-gel template approach *Journal of the American Chemical Society*, **126(19)**: 5976–5977.

[3] Yada, M.; Mihara, M.; Mouri, S.; Kuroki, M. and Kijima, T. (2002). Rare earth (Er, Tm, Yb, Lu) oxide nanotubes template by dodecyl sulfate assemblies. *Advanced Materials*, **14(4)**: 309–313.

[4] Vantomme, A.; Yuan, Z. Y.; Du, G. and Su, B. L. (2005). Surfactant assisted large-scale preparation of crystalline CeO_2 nan rods. *Langmuir***, 21(3)**: 1132–1135.

[5] Zhang, J. and Hong, G. (2004). Synthesis and photoluminescence of the Y_2O_3:Eu^{3+} phosphor nanowires in AAO template. *Journal of Solid State Chemistry*, **177(4-5)**: 1292–1296.

[6] Oskam, G. (2006). Metal oxide nanoparticles: synthesis, characterization and applicatio. *Journal Sol-Gel Science Technol*ogy**, 37**: 161.

[7] Aldebert, P. and Traverse, J. P. (1979). Etudepar diffraction neutroniquedes structures de haute temperature de La_2O_3 et Nd_2O_3. Mater.Res.Bull,**14**: 303–323 .

[8] Zinkevich, M. (2007). Thermodynamics of rar earth sesquioxides. Prong Master Science, **52**:597-647.

[9] Romero, J. *et al* . (2007). Nephrogenic systemic fibrosis: a case series suggesting gadolinium as a possible a etiological factor. *British Journal of Dermatology*, **157**: 783-787.

[10] Kabalka, G.; Buonocore, E.; Hubner, K.; Davis, M. and Huang, L. (1988). Gadolinium labeled liposomes containing paramagnetic amphipathic agents: Targeted MRI contrast agents for the liver. *Magnetic resonance in medicine***, 8**: 89-95.

[11] Kralchevsky, P. A. and Nagayama, K. (2000). Capillary interactions between particles bound to interfaces, liquid films and bio membranes. Advantage Colloid Interface Science, **85**:145 .

[12] García, A.; Espinosa, R.; Delgado, L.; Casals, E.; Gonz_alez, E.; Puntes, V.; Barata, C.; Font, X. and _anchez, A. S. (2011). Acute toxicity of cerium oxide, titanium oxide and iron oxide nanoparticles using standardized tests. *Desalination*, **269**:136-141.

[13] Guoa, H.; Yangb, X.; Xiaob, T.; Zhanga, W.; Loub, L. and Mugnierc, J. (2004). Structure and optical properties of sol–gel derived Gd_2O_3 waveguide films. *Applied Surface Science*, **230** : 215–221

[14] Jusoh, S. N.; S. Taking, S.; Jamal, Z. and Idris, M. A.(2009)**.** Surface roughness and grain size

characterization of annealing temperature effect for growth gallium and tantalum doped Ba $_{0.5}$ Sr $_{0.5}$ TiO_3 thin film. *Atom Indonesia*, **35 (1)** .
[15] Guoa, H.; Yang, X.; Xiao, T.; Zhanga, W.; Loub, L.; Jacques Mugnierm, J.(2004). Structure and optical properties of sol–gel derived Gd_2O_3 waveguide films .*Applied Surface Science*, **230**: 215–221.
[16] Jayakumar, S.; T. Saravanan, T. and Philip, J. (2017). Preparation, characterization and X-ray attenuation property of Gd_2O_3-based Nano composites. *Applied Nanoscience*, **7**:919–931.
[17] Ahrén, M.; Selegård, L.; Söderlind, F.; Linares, M.; Joanna Kauczor, J.; Norman, P.; Käll, PO. and Uvdal, K. (2012). A simple polyol-free synthesis route to Gd_2O_3 nanoparticles for MRI applications: an experimental and theoretical study. *Journal. Nanopart*icle Research, 14: 1-17.
[18] Zhu, J.; Deng, C.; Liu, Y.; Lin, N. and Liu, S. (2019). Effects of Annealing Temperature on Recrystallization Texture and Microstructure Uniformity of High Purity Tantalum. *Metals,(9)* :75.
[19] Lux, F.; Sancey, L.; Bianchi, A.; Crémillieux, Y.; Roux, S. and Tillement, O. (2015). Gadolinium-based nanoparticles for theranostic MRI-radiosensitization. *Nanomedicine*. **10(**11) :1801-1815.
[20] Dikhell, R. H. A. (2018). Study of Some Physical Properties Of Laser Energies For CuO and CdO Nano Particles and their Antibacterial Effect. M.Sc , University of Tikrit, College of Education for pure Sciences, Department of Physics.
[21] Jamnezhad, H. and Jafari, M. (2016). Structure of Gd_2O_3 nanoparticles at high temperature. *Journal of Magnetism and Magnetic Materials* ,**408**: 164–167.
[22] Cowburn, R. P. (2000). Property variation with shape in magnetic nanoelements. *Journal of Physics D: Applied Physics*, **33**: 1–16.

الخصائص النمائية والتركيبية والمغناطيسية لأغشية أكسيد الجادولينيوم (Gd2O3)

هدى سعدي علي ، نديم خالد حسن

قسم الفيزياء ، كلية التربية للعلوم الصرفة ، جامعة تكريت ، تكريت ، العراق

الملخص

تم الحصول على طبقة رقيقة من الأغشية النانوية Gd_2o_3 من خلال تقنية الطلاء الدوراني. وتم قياس الخواص التركيبية للغشاء الرقيق بتقنة حيود الأشعة السينية(XRD) لمعرفة التركيب البلوري وتأثير اختلاف درجات حرارة التلدين المختلفة على النمو البلوري لتلك النماذج، وفحوصات المجهر الإلكتروني الماسح(SEM) وتم دراسة الخواص المغناطيسية بأستخدام مقياس المغنطيسية لعينة اهتزازية (VSM) في درجات حرارة التلدين المختلفة (500،600،700،800) سيليزية. وبينت نتائج حيود الاشعة السينية بأن جميع الاغشية المحضرة ذات تركيب متعدد التبلور ذات قيم حيود واتجاهات مختلفة وكانت اغشية Gd_2O_3 من النوع المكعب ولوحظ انه بزيادة درجة حرارة التلدين نحصل على افضل أنماء بلوري وبينت نتائج SEM ان شكل الحبيبات النانوية المرسبة كانت بشكل كروي ،ونلاحظ زيادة مغنطة التشبع (MS) بحوالي (0.1811 − 0.1421) emu / g مع زيادة درجة حرارة التلدين.