

Development of Mathematical Models for Prediction of Some Mechanical Properties of High Strength Concrete Exposed to Burning

Mohammad Mansour Kadhum

Babylon University, College of Engineering, Department Of Civil Engineering

Abstract

This research work is aims to develop mathematical models for prediction of the some mechanical properties of high strength of concrete after burning by fire flame. These models used linear and non-linear regression equations by statistical program called (*DATA FIT 9.0.59, 2009*) to evaluate good coefficient correlation with fewer variables introduced in them. The concrete specimens were subjected to fire flame temperatures ranging from (25-850 °C) at different ages of 30, 60 and 90 days. Three temperature levels of 400°C, 600°C and 850°C were chosen of exposure duration of 2.0 hours. After burning, the concrete specimens were quenched in a water tank to provide the maximum shock due to sudden cooling. The test results showed that the density, compressive strength, tensile and flexural strength decreases when the fire flame temperatures were increased. Mathematical models were proposed to predict the compressive strength, splitting tensile strength and flexural strength of concrete after exposure to fire flame. The compressive strength test results of this study together with results obtained by other investigators were compared with CEB strength reduction curve and that of CEN. It was noticed that the test results agreed with CEN design curve rather than with that of CEB.

الخلاصة

يهدف هذا البحث إلى بناء نماذج رياضية للتنبؤ لبعض خصائص الخرسانة ذات المقاومة العالية بعد التعرض للحرق بلهب النار المباشر. هذه الموديلات تعتمد على معادلات خطية وغير خطية متعددة المتغيرات للحصول على قيم تخمينية مع أيجاد معامل ارتباط جيد بين هذه الخواص باستخدام بعض المعلومات عن الخواص الميكانيكية للخرسانة قبل تعرضها إلى لهب النار. عرضت النماذج الخرسانة إلى درجات حرارة تتراوح بين (25-850) درجة مئوية وبأعمار مختلفة هي (30, 60, 90) يوما حيث تم تعريض النماذج إلى ثلاث درجات حرارية (400, 600, 850) درجة مئوية ولمدة ساعتين. بعد التعرض بردت النماذج بالماء لوحظ من النتائج أن مقاومة الخرسانة للانضغاط والشد والانثناء تتناقص بزيادة درجة الحرارة. تم استخدام برنامج إحصائي (*Data Fit*) لتخمين خصائص الخرسانة المعرضة للحرق. قورنت النتائج العملية لمقاومة الانضغاط المعرضة إلى لهب النار في الدراسة الحالية مع بعض نتائج الدراسات الأخرى مع منحنيين مقترحين من قبل المدونات الأوروبية لتقييم نقصان المقاومة بتأثير درجات الحرارة فوجد أن النتائج العملية متوافقة أقرب مع توصيات المدونة الأوروبية (CEN) عن (CEB).

Introduction

In the structural design of buildings, in addition to the normal gravity and lateral loads, it is in many cases necessary to design the structure to safely resist exposure to fire. However it is usually necessary to guard against structural collapse for a given period of time Kadhum (2010).

Several investigations have shown that the deterioration in the compressive strength of concrete under high temperature exposure. There are indeed rare researches about temperature gradient and exposure time of the concrete indirect contact with the fire flames. In this study there is an attempt to investigate the effect of temperature gradient and exposure of high strength concrete to fire flames on compressive strength, tensile strength and flexural strength of high strength concrete. Also, suggesting empirical formula to

obtain these properties by using statistical regression analysis program called (*DATA FIT 9.0.59, 2009*) based on the experimental results before and after burning.

Fire Effect on The Mechanical Properties of Concrete

Maltora (1956), Davis (1967), Abrams (1971), Faiyadh (1989), Khoury (1992) and Noumowe *et al* (1994) had reported the effects of high temperature exposure on the properties of concrete. Several mechanisms have been identified for the deterioration of concrete due to high temperature. These include decomposition of the calcium hydroxide with time and water, expansion of lime on re-hydration, destruction of gel structure, phase transformation in some types of aggregate, and development of micro-cracks due to thermal incompatibility between cement paste matrix and aggregate phase.

High strength concrete, in comparison with medium strength concrete, is more brittle; contains less water; and the solid particles are more compact. Hence, the effects of high temperature on high strength concrete will be different to those with the medium strength concrete. Sri Ravindarajah (1998) studied the effect of temperature up to 800°C and method of cooling on the compressive and tensile strength of high-strength concrete .

Habeeb in (2000) studied the effect of high temperatures (up to 800°C) on some mechanical properties of high strength concrete (HSC). Three design strength investigated 40, 60 and 80MPa. The investigated properties were compressive strength, flexural strength and volume changes. Ultrasonic pulse velocity (U.P.V) and dynamic modulus of Elasticity (E_d) were tested also. The specimens were heated slowly to five temperatures levels (100, 300, 500, 600 and 800°C), and to three exposure periods 1.0, 2.0 and 4.0 hours without any imposed loads during heating. The specimens were then cooled slowly and tested either one day or one month after heating. He concluded that the (HSC) is more sensitive to high temperatures than(NSC). The residual compressive strength ranged between (90-106 %) at 100°C, (72-103 %) at 300°C, (55-87 %) at 500°C and (22-66 %) between (600-800 °C). He concluded that exposure time beyond one hour had a significant effect on the residual compressive strength of concrete; however, the effect was diminished as the level of temperature increased. Moreover, the compressive strength at age of one month after heating, suffered an additional less than at age of one day after heating. The flexural strength was found to be more sensitive to high temperature exposure than compressive strength the residual flexural strength was in the range of (92- 98 %), (52-98 %) and (29-47 %) at 100°C, 300°C, and 500°C respectively and (2-30 %) at (600-800)°C. The author also noticed that the (U.P.V) and (E_d) were more sensitive to elevated temperature to exposure than compressive strength.

Husem (2006) examined the variation in compressive and flexural strengths of ordinary and high-performance concretes exposed to high temperatures of 200, 400, 600, 800 and 1000°C and then cooled in air or water. The compressive and flexural strengths of these concrete specimens were compared with each other and with unheated specimens. On the other hand, strength loss curves of these concrete specimens were compared with the strength loss curves given in the codes. In this study, ordinary concrete with an average

compressive strength of 34MPa and high-performance concrete with an average compressive strength of 71MPa were produced. From the results obtained, he concluded that the compressive strength of high-performance concrete cooled in air and water decreases up to 200°C and increases between 200 and 400°C. The compressive strength gain was 13% for the specimens cooled in air and 5% for those cooled in water.

Saqier, 2008 investigated the effect of fire flame exposure on properties of normal and high performance concrete. The specimens were subjected to fire flame ranging between (25-700°C). Two temperature levels of (400 and 700 °C) were chosen with two different exposure duration of (1, 1.5) hours without any imposed loads during heating. The specimens were heated and cooled either by air or water.

He found that :

- 1- The percentage residual compressive strength for NSC and HPC ranged between (77-84%) and (51-73%) at 400°C, (29-65%) and (40-50%) at 700°C respectively.
- 2- The splitting tensile strength is more sensitive to fire flame exposure than the compressive strength. The percentage residual for HPC at (400°C and 700°C) is about (61-78%) and (37-40%) respectively, while the percentage residual for NSC at (400°C and 700°C) is about (50-80%) and (41-51%) respectively.
- 3- The flexural strength is more sensitive to fire flame temperatures than compressive strength and splitting tensile strength. The percentage residual flexural strength for HPC after exposure to (400°C and 700°C) is about (34-40%) and (13-21%) respectively, while the percentage residual flexural strength for NSC at (400°C and 700°C) is about (37-42%) and (16-27%) respectively.

Experimental Work

- Introduction

The experimental work was carried out to decide upon the temperature range and duration of burning. It was decided to limit the maximum exposure to fire to about 400°C, 600°C and 850°C with a duration of exposure to fire flame of 2.0 hours which cover the range of situation in the majority of elevated temperature test.

- Material and Mixture properties

In this investigation, the cement used Ordinary Portland Cement (O.P.C) produced at Kufa factory. This cement complied with the Iraqi specification No.5 (1984). Testing of cement was conducted in the laboratories of Consultant Engineering Bureau in Babylon University. The physical properties and chemical compositions are presented in Table(1). Crushed basalt (specific gravity of 2.65) having the maximum aggregate size of 10mm and river sand (specific gravity of 2.62) were used as a coarse and fine aggregate content was 30% , by weight.

Three mixes were investigated mix 1 consisted 535Kg/m³ of cement. In mix 2, 20% fly ash and 80% cement (O.P.C) (fly ash was replaced from cement). Mix 3 contained 90% (O.P.C) and 10% silica fume (silica fume was replaced from cement). For all three mixes the water to cement ratio was kept at 0.30 by weight. A constant dosage of super

plasticizers (1.0% by weight of cement) was used in all concrete mixture to obtain workable concrete mixtures.

Table (1) : A- Physical properties of the cement.

Physical properties	Test results	IQS (No.5: 1984) Limits
Fineness ,Blaine ,cm ² /gm	3180	≥ 2300
setting time, vicat's method		
initial hrs : min.	1:40	≥ 1:0
final hrs : min.	3:60	≤ 10:00
compressive strength of 70.7mm cube ,MPa		
3 days	24	≥ 15
7 days	29	≥ 23

B- Chemical composition of the cement.

Oxide	Percentage %	IQS (No.5: 1984) Limits
CaO	60.76	
SiO ₂	20.20	
Fe ₂ O ₃	3.30	
Al ₂ O ₃	6.20	
MgO	4.24	≤ 0.5
SO ₃	2.34	≤ 2.8
Free lime	0.72	
L.O.I	1.63	≤ 4.0
I.R.	0.61	≤ 1.5
Compound composition	Percentage %	IQS (No.5: 1984) Limits
C ₃ S	37.50	
C ₂ S	30.85	
C ₃ A	10.65	
C ₄ AF	8.42	
L.S.F	0.82	0.66-1.02

- Concrete Mixing and Casting

Mixing of concrete was performed according to the (ASTM C192-1995). The concrete mixture were produced in a horizontal pan-type mixer of 0.1m³ capacity. The interior surface of mixer was cleaned and moistened before it was used. Freshly mixed concrete was tested for its density and used to cast a number of test specimens (standard cubes, cylinders and prisms) in steel moulds. The concrete specimens were cast in two layers, compacting each layer was conducted for fifteen seconds using a vibrating table. A table vibrator was used to achieve full compaction for the moulded test specimens. After casting and compacting, the top surface of the specimens were smoothed. The specimens used for compressive strength (100×100×100)mm cube and for tensile strength (100mm diameter by 200mm long) cylinder. The specimens used for flexural strength (100×100×400)mm prisms.

- Burning and Cooling

The concrete specimens were burn with direct fire flame from a net of methane burners inside a brick stove with dimensions of (800×800×1000 mm) (length × width × height respectively) as shown in plate (1). The bars of flame were intended to simulate the heating condition in an actual fire. When the target temperature was reached, the temperature was continuously measured by applying Infrared ray thermometer from about approximately 2 meters from the concrete exposed to fire. The measurement device is shown in plate (2). After burning, the concrete specimens were quenched in a water tank to provide the maximum thermal shock due to sudden cooling.



Plate(1): Brick stove of network of methane burners.



Plate(2): Temperature measurements devices.

Results and Discussion

-The Density

Table (2) show the effect of the exposure to fire flame on the density of high strength concrete, while Figures (1 to 3) shows the relations between the fire flame temperature and density of high strength concrete. It can be seen from these table and figures that the density behaved as the following :

- 1- At (400, 600 and 850°C) fire flame temperature exposure and for all ages and for mix 1, the reduction in density was ranged between (1.8-2.8%), (3.6-5.5%) and (6.8-9.2%) respectively if compared with initial density before exposure to fire flame.
- 2- At (400, 600 and 850°C) fire flame temperature exposure and for all ages and for mix 2, the reduction in density less than reduction in mix 1 was ranged between (1.4-2.0%), (2.8-4.2%) and (5.6-8.6%) respectively.
- 3- In mix 3, the reduction in density less than reduction in mix (1 and 2) was (1.0-1.5%), (2.0-3.1%) and (4.2-6.8%) at (400, 600 and 850°C) respectively for the same fire flame temperature. These results confirmed that of Sri Ravindrarajah (1993) and Karim (2005).

Table (2): Test values of density of high-strength concrete for all mixes before and after exposure to fire flame.

Age at exposure (days)	Mix NO.	Density (Kg/m ³)				Ratios ρ_a/ρ_b		
		Temperature °C				2/1	3/1	4/1
		25 (1)	400 (2)	600 (3)	850 (4)			
30	Mix 1	2420	2235	2167	2112	0.92	0.89	0.87
	Mix 2	2380	2212	2134	2092	0.93	0.90	0.88
	Mix 3	2640	2495	2347	2297	0.95	0.89	0.87
60	Mix 1	2415	2237	2169	2115	0.92	0.90	0.88
	Mix 2	2370	2216	2137	2095	0.94	0.90	0.88
	Mix 3	2632	2499	2349	2299	0.95	0.89	0.89
90	Mix 1	2411	2241	2172	2117	0.93	0.90	0.88
	Mix 2	2365	2219	2139	2097	0.94	0.90	0.89
	Mix 3	2625	2502	2351	2301	0.95	0.90	0.88

ρ_a = Density of concrete after exposure to fire flame.

ρ_b = Density of concrete before exposure to fire flame.

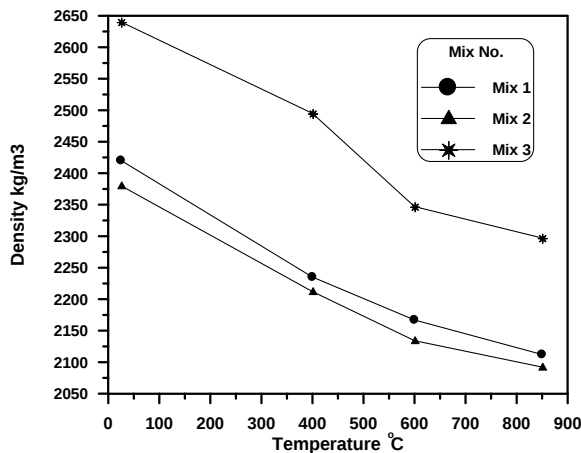


Figure (1): The effect of fire exposure on the density of high-strength concrete at age 30 days and 2.0 hours period of exposure.

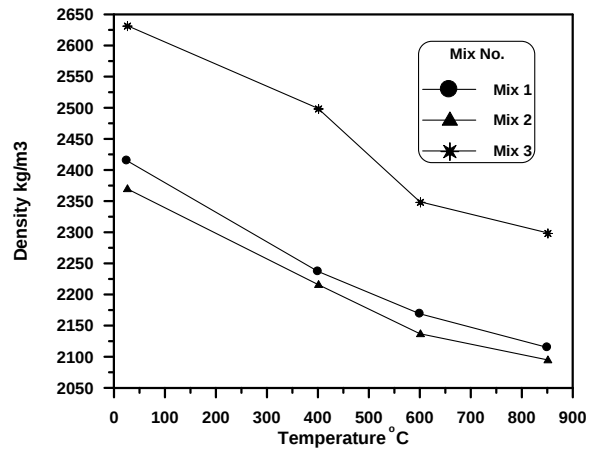


Figure (2): The effect of fire exposure on the density of high-strength concrete at age 60 days and 2.0 hours period of exposure.

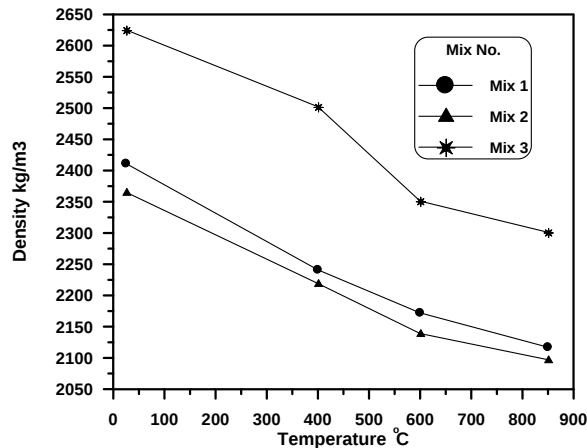


Figure (3): The effect of fire exposure on the density of high-strength concrete at age 90 days and 2.0 hours period of exposure.

Effect of Temperature on Compressive Strength

Concrete cubes (100×100×100mm) were tested at ages 30, 60 and 90 days. The compressive strength results are summarized in Table (3), while the Figures (4, 5 and 6) shows the relation between the compressive strength and fire flame temperature for different ages. The compressive strength of the high strength concrete dropped significantly as the maximum temperature was increased. The residual strength varied from (71-89%) of the corresponding initial strength when the concrete was exposed to the fire flame was 400°C followed by sudden cooling in water. As the temperature was increased to 600°C, the residual strength was ranged from (46-81%) of the initial strength. At 850°C fire flame temperature exposure the residual strength ranged from (29-45%).

The results showed that the binder material type has noticeable influence on the residual strength. The concrete mixture containing silica fume performed poorly compared to other binder materials. Although the silica fume addition increased the initial strength of concrete, considerable compressive strength loss when exposed to fire flame temperature is noticed. It is observed that the color of the concrete specimens changed to pink and increased in intensity. This may be due to hydration condition of iron oxide component and other material constituents of the fine and coarse aggregates, Habeeb (2000). The surface cracks increased in number length and depth due to temperature rise.

Table (3): Test values of compressive strength of high strength concrete for all mixes before and after exposure to fire flame.

Age at exposure (days)	Mix No.	Compressive strength (MPa)				Ratios fca/fcb		
		Temperature °C						
		25 ₍₁₎	400 ₍₂₎	600 ₍₃₎	850 ₍₄₎	2/1	3/1	4/1
30	Mix 1	42.4	30.1	19.5	12.3	0.71	0.46	0.29
	Mix 2	52.5	43.6	34.2	19.9	0.83	0.65	0.38
	Mix 3	57.0	49.0	43.3	23.4	0.86	0.76	0.41
60	Mix 1	44.0	32.0	20.7	12.3	0.73	0.47	0.28
	Mix 2	55.2	49.1	38.0	21.5	0.89	0.69	0.39
	Mix 3	59.8	52.6	47.2	25.7	0.88	0.79	0.43
90	Mix 1	45.3	33.0	22.2	13.6	0.73	0.49	0.30
	Mix 2	57.0	50.7	39.9	24.0	0.89	0.70	0.42
	Mix 3	61.2	54.4	49.6	27.6	0.89	0.81	0.45

fca = Compressive strength after exposure to fire flame .

fc_b = Compressive strength before exposure to fire flame .

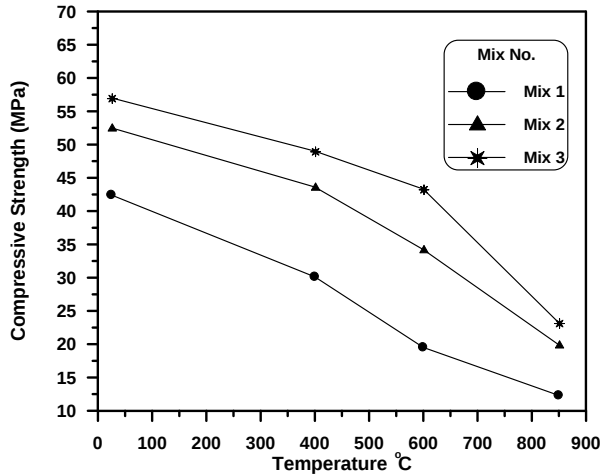


Figure (4): The effect of fire exposure on the compressive strength of high-strength concrete at age 30 days and 2.0 hours period of exposure.

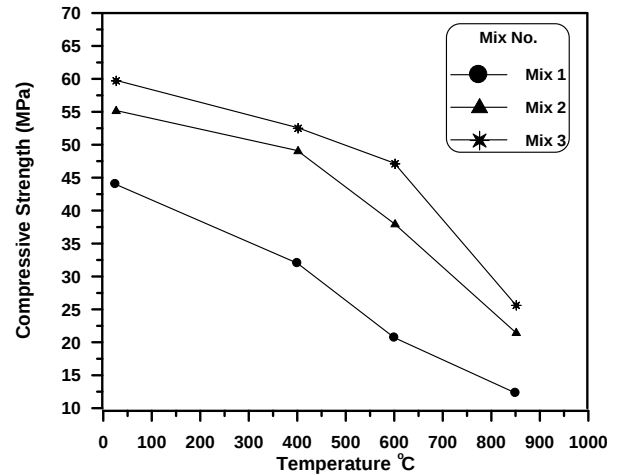


Figure (5): The effect of fire exposure on the compressive strength of high-strength concrete at age 60 days and 2.0 hours period of exposure.

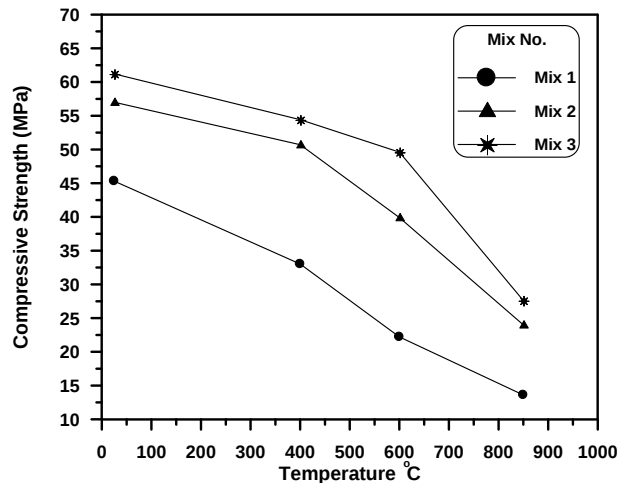


Figure (6): The effect of fire exposure on the compressive strength of high-strength concrete at age 90 days and 2.0 hours period of exposure.

-Comparison Between Residual Compressive Strength Results and Recommended Design Curves (CEB & CEN)

Euro-Code Nos.2 and 4 (Committee European de Normalization) (CEN) (1993,1994), specified rules for strength and deformation properties of uniaxially stressed, normal weight aggregate (NWA) (siliceous and calcareous) concrete at temperatures up to 1200°C. The CEB Bulletin D' Information No.208 (CEB) (1991), recommended design curves for compressive strength of siliceous (NWA) concrete based on the work of many investigators. The residual compressive strength results obtained from tests carried out by many researchers in addition to the present study are plotted with the CEN and CEB design curves as shown in Figure(7). It can be seen that the temperature range between (200-

300°C) is characterized by a maximum residual strength (Malhotra, 1956) , (Abrams, 1971), (Al-Ausi and Faiyadh, 1985) and (Al-Owaisy, 2001). Improvement in compressive strength is observed to a maximum value in temperatures ranged between (100-150°C) (Al-Ausi and Faiyadh, 1985), and (Habeeb, 2000). This behavior is attributed to the cement paste response due to causing weakening of bond in the range between (50-150°C), thereafter, densification due to thermal drying contributed to the increase of strength. Beyond 300°C, there is a further reduction in compressive strength. In the present study some of the test results of residual compressive strength were found to lie between CEB and CEN curves, while other results diverged from the CEB curve and converged to the CEN curve especially at 400°C of fire exposure. At 600°C and 850°C, the test results were found to be near the CEN curve only. From the figure, it can be concluded that the test results of the current study have better agreement with CEN design curve than with CEB curve.

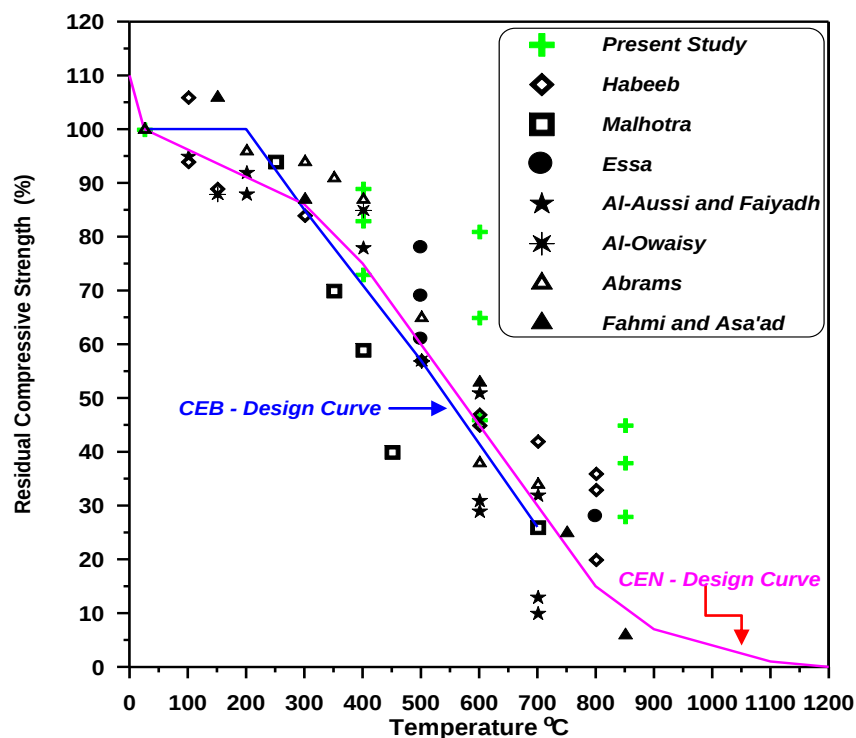


Figure (7): Comparison of residual compressive strength results and the recommended design curves of CEB and CEN.

-Effect of Temperature on Tensile and Flexural Strengths

Figures (8, 9 and 10) show the residual tensile for high strength concrete as a function of the maximum temperature. Similar to the compressive strength, the tensile strength showed significant losses with the increase in the exposed temperature. Once again, the binder material types played a noticeable role in influencing the strength losses. The results shown in Figures (8, 9 and 10) indicated that the mix 3 having silica fume suffered significant loss in strength at the temperature of 600°C. The tensile strength for high

strength concrete mixes was reduced by 78% to 84% when they were burn to 850°C. These result are summarized in Table (4).

The flexural strength for all three concrete mixes are presented in Table (5), while figure (11, 12 and 13) show the effect of fire flame exposure of flexural strength. Similar to compressive and tensile strengths of concrete, the flexural strength decreased with temperature. Once again the binder material type had influenced the extent of strength loss.

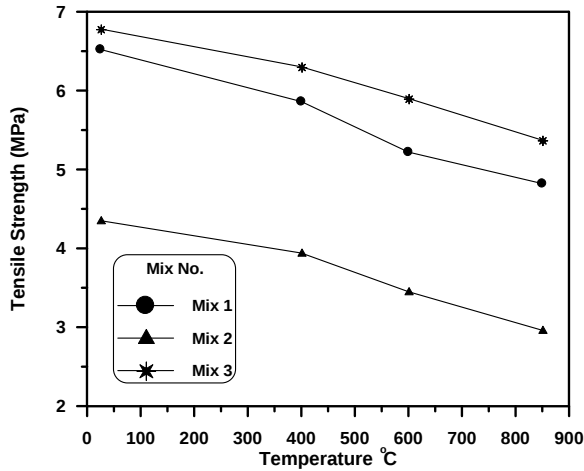


Figure (8): The effect of fire exposure on the tensile strength of high-strength concrete at age 30 days and 2.0 hours period of exposure.

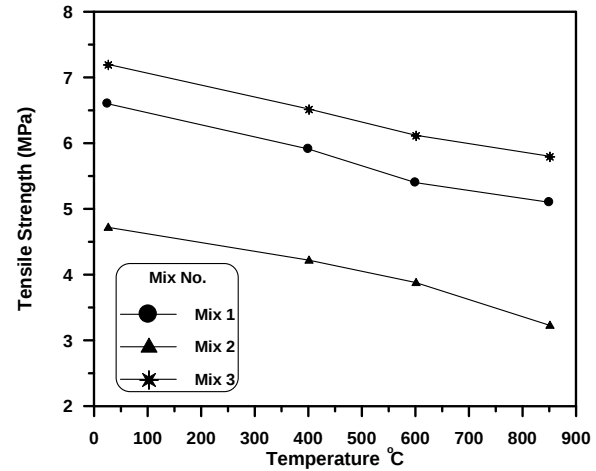


Figure (9): The effect of fire exposure on the tensile strength of high-strength concrete at age 60 days and 2.0 hours period of exposure.

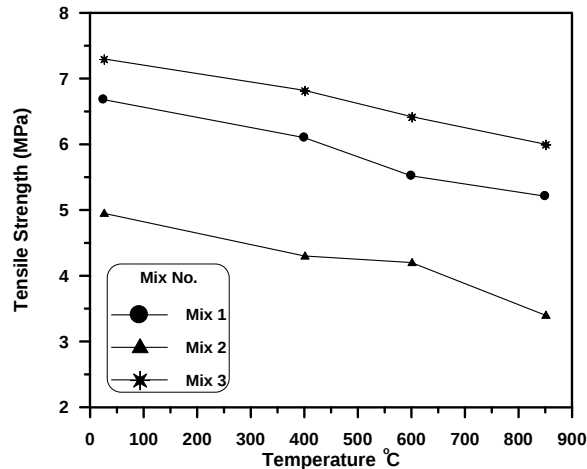


Figure (10): The effect of fire exposure on the tensile strength of high-strength concrete at age 90 days and 2.0 hours period of exposure.

Table (4): Test value of tensile strength f_t high strength concrete for all mixes before and after exposure to fire flame.

Age at exposure (days)	Mix No.	Tensile strength (MPa)				Ratios Tsa/Tsb		
		Temperature °C						
		25 ₍₁₎	400 ₍₂₎	600 ₍₃₎	850 ₍₄₎	2/1	3/1	4/1
30	Mix 1	6.25	5.86	5.22	4.82	0.90	0.80	0.74
	Mix 2	4.35	3.94	3.45	2.96	0.90	0.79	0.68
	Mix 3	6.78	6.30	5.90	5.37	0.93	0.87	0.79
60	Mix 1	6.60	5.91	5.40	5.10	0.89	0.82	0.77
	Mix 2	4.72	4.22	3.88	3.23	0.89	0.82	0.68
	Mix 3	7.20	6.52	6.12	5.80	0.90	0.85	0.80
90	Mix 1	6.68	6.10	5.52	5.21	0.91	0.83	0.80
	Mix 2	4.95	4.30	4.20	3.40	0.87	0.87	0.69
	Mix 3	7.30	6.82	6.42	6.00	0.93	0.88	0.82

Tsa = Tensile strength after exposure to fire flame.

Tsb = Tensile strength before exposure to fire flame.

Table (5): Test values of flexural strength of high strength concrete for all mixes before and after exposure to fire flame.

Age at exposure (days)	Mix No.	Flexural strength (MPa)				Ratios Fsa/Fsb		
		Temperature °C						
		25 ₍₁₎	400 ₍₂₎	600 ₍₃₎	850 ₍₄₎	2/1	3/1	4/1
30	Mix 1	9.22	8.39	7.86	7.45	0.90	0.85	0.80
	Mix 2	6.64	5.80	5.12	4.76	0.87	0.77	0.71
	Mix 3	8.30	7.42	6.95	6.30	0.89	0.84	0.80
60	Mix 1	9.40	8.50	7.94	7.65	0.90	0.84	0.81
	Mix 2	6.88	6.02	5.50	4.90	0.88	0.80	0.71
	Mix 3	8.92	7.80	7.20	6.50	0.87	0.80	0.73
90	Mix 1	9.72	8.72	8.25	7.75	0.89	0.85	0.80
	Mix 2	7.01	6.48	5.82	5.12	0.92	0.83	0.73
	Mix 3	9.12	7.95	7.40	6.81	0.87	0.81	0.75

Fsa = Flexural strength after exposure to fire flame.

Fsb = Flexural strength before exposure to fire flame.

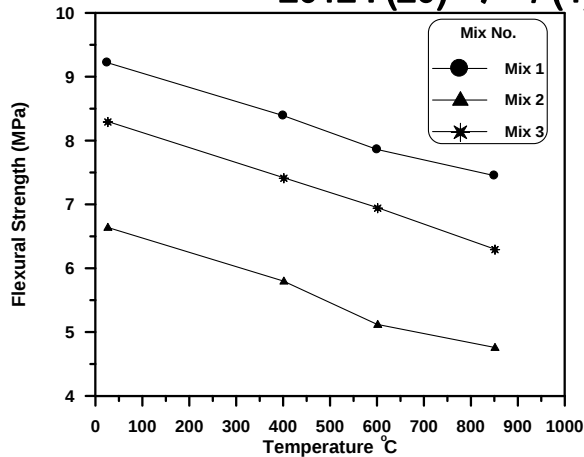


Figure (11): The effect of fire exposure on the flexural strength of high-strength concrete at age 30 days and 2.0 hours period of exposure.

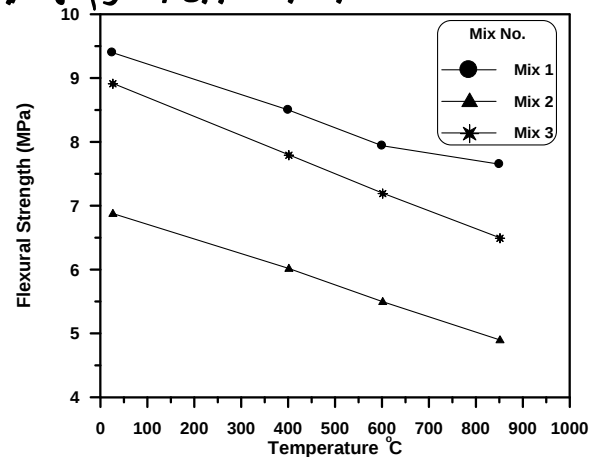


Figure (12): The effect of fire exposure on the flexural strength of high-strength concrete at age 60 days and 2.0 hours period of exposure.

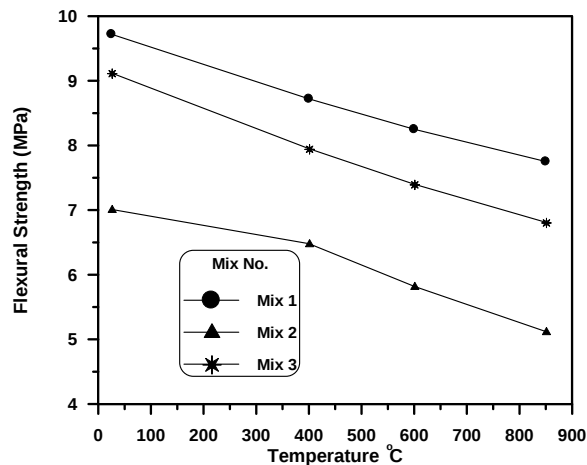


Figure (13): The effect of fire exposure on the flexural strength of high-strength concrete at age 90 days and 2.0 hours period of exposure.

-Effect of Exposure Fire Flame on The Colour of Concrete

Since the thermal conductivity reduces with the increase in temperature water quenching of the heated concrete samples has not produced uniform cooling. At the temperature of 400°C, there was no apparent visual discoloration occurred in the concrete. The concrete specimens subjected to 600°C and above suffered noticeable color change. The inner section of the concrete bluish in colour. The dark colored area boundary was very distinct and showed no transition zone. Outside this, concrete had maintained its color however, when the fire flame temperature was increased to 850°C the inner color was changed to bluish dark grey.

- Mathematical Models for Prediction of Mechanical properties of Concrete After Exposure to Fire Flame

In order to obtain an accurate mathematical model that can predict mechanical properties of high strength of concrete after burning, nonlinear regression is used for this purpose. The analysis of the experimental results utilized the regression analysis to obtain

multiple models and choosing the best mathematical model which require the highest correlation coefficient. By using the data which was obtained from this study, mathematical models were proposed to predict the compressive strength, splitting tensile strength and flexural strength of concrete after exposure to fire flame. These models made by statistical program called (*DATA FIT 9.0.59, 2009*) and depends on compressive strength, splitting tensile strength and flexural strength of concrete before and after burning, age and temperature of fire flame.

The first step in the development of the statistical analysis was the selection of the variables include in model prediction. The independent dependent variables were selected as shown in Table (6).

Table (6): Dependent and independent variables.

Dependent Variables	Independent Variables
f_{cua}	f_{cub}, Age, T, ρ
f_{sa}	f_{sb}, Age, T, f_{cu}
f_{ra}	f_{rb}, Age, T, f_{cu}

• Models for Prediction of Compressive Strength (f_{cua})

Three models were examined to predict of (f_{cua}) after burning as follows:

1. The first models :

$$f_{cua} = \exp(a \times f_{cub} + b \times Age + c \times T + d \times \rho + e)$$

Where:

f_{cua} = Compressive strength of the specimens after exposure to fire flame temperature (MPa).

f_{cub} = Compressive strength of the specimens before exposure to fire flame temperature (MPa).

Age = The age of the specimens at the time of exposure (days).

T = Temperature of fire flame (°C).

ρ = Density of concrete before and after exposure to fire flame (kg/m³).

a, b, c, d, e = Regression coefficients of independent variables.

2. The second model :

$$f_{cua} = a \times f_{cub} + b \times Age + c \times T + d \times \rho$$

3. The third model:

$$f_{cua} = a \times f_{cub} + b \times Age + c \times T + d \times \rho + e$$

• Models for Prediction of Splitting Tensile Strength (f_{sa})

Three models were examined to predict of (f_{sa}) after burning as follows:

1. The first model:

$$f_{sa} = \exp(a \times f_{sb} + b \times Age + c \times T + d \times f_{cub} + e)$$

Where:

f_{sa} = Splitting tensile strength of the specimens after exposure to fire flame temperature (MPa).

f_{sb} = Splitting tensile strength of the specimens before exposure to fire flame temperature (MPa).

Age = The age of the specimens at the time of exposure (days).

T = Temperature of fire flame (°C).

f_{cub} = Compressive strength of the specimens before and after exposure to fire flame temperature (MPa).

a, b, c, d, e = Regression coefficients of independent variables.

2. The second model :

$$f_{sa} = a \times f_{sb} + b \times Age + c \times T + d \times f_{cub}$$

3. The third model :

$$f_{sa} = a \times f_{sb} + b \times Age + c \times T + d \times f_{cub} + e$$

- Models for Prediction of Flexural Strength (f_{ra})

To find the regression for prediction of (f_{ra}) after burning three models were as follows:

1. The first model :

$$f_{ra} = \exp(a \times f_{rb} + b \times Age + c \times T + d \times f_{cub} + e)$$

Where:

f_{ra} = Modulus of rupture of the specimens after exposure to fire flame temperature (MPa).

f_{rb} = Modulus of rupture of the specimens before exposure to fire flame temperature (MPa).

Age = The age of the specimens at the time of exposure (days).

T = Temperature of fire flame (°C).

f_{cub} = Compressive strength of the specimens before and after exposure to fire flame temperature (MPa).

a, b, c, d, e = Regression coefficients of independent variables.

2. The second model :

$$f_{ra} = a \times f_{rb} + b \times Age + c \times T + d \times f_{cub}$$

3. The third model :

$$f_{ra} = a \times f_{rb} + b \times Age + c \times T + d \times f_{cub} + e$$

Table (7) gives the regression coefficients of the prediction models above for the prediction of the compressive strength, splitting tensile strength and flexural strength of concrete after exposure to fire flame.

From the same table, the correlation coefficient increases and the standard error decreases with increasing the number of factors used in the proposed model.

Table (7): Regression coefficients for mechanical properties of concrete after burning.

1. f_{cu}

Coefficient	Model 1	Model 2	Model 3
a	0.032513	1.20969	1.21525
b	-0.000364	-0.004753	-0.005179
c	-0.000957	-0.039192	-0.039796
d	-0.000242	-0.003225	-0.004703
e	2.88643	-----	3.423845
Variance Explained (R^2)	0.8547	0.9012	0.9283
Standard Error	5.9184	4.1971	4.1595

2. f_{sa}

Coefficient	Model 1	Model 2	Model 3
a	0.193225	0.980034	0.98577
b	-0.000210	-0.000974	-0.00097
c	-0.000299	-0.001541	-0.001541
d	0.000260	0.004840	0.00560
e	0.620608	-----	-0.08118
Variance Explained (R^2)	0.9110	0.9322	0.9858
Standard Error	0.36753	0.2476	0.1432

3. f_{ra}

Coefficient	Model 1	Model 2	Model 3
a	0.13438	1.00638	0.925041
b	-0.000147	-0.000272	0.000430
c	-0.000347	-0.002419	-0.002841
d	-0.000515	4.83152	-0.009862
e	1.035120	-----	1.21353
Variance Explained (R^2)	0.9021	0.9821	0.9890
Standard Error	0.1906	0.1788	0.1495

The increase of correlation coefficient and decrease in standard error from model (1) to model (3), proves the right choice of the variables and their effect on compressive strength, splitting tensile strength and flexural strength of concrete after burning. Also it

can be seen from Figures (13) to (15) the difference between experimental data and calculated data of mechanical properties of concrete before and after burning in model (3).

From Table (7), it can be seen that model (3) represents the best model fits to the experimental data due to the higher coefficient of determination (R^2). Therefore, the following models could be used to estimate the compressive strength, splitting tensile strength and flexural strength of concrete after exposure to fire flame.

$$f_{cua} = 1.21525 \times f_{cub} - 0.005178 \times Age - 0.039796 \times T - 0.00470 \times \rho + 3.423845$$

$$f_{sa} = 0.98577 \times f_{sb} - 0.00097 \times Age - 0.001541 \times T + 0.00560 \times f_{cub} - 0.081183$$

$$f_{ra} = 0.92504 \times f_{rb} + 0.00043 \times Age - 0.002841 \times T - 0.00986 \times f_{cub} + 1.21353$$

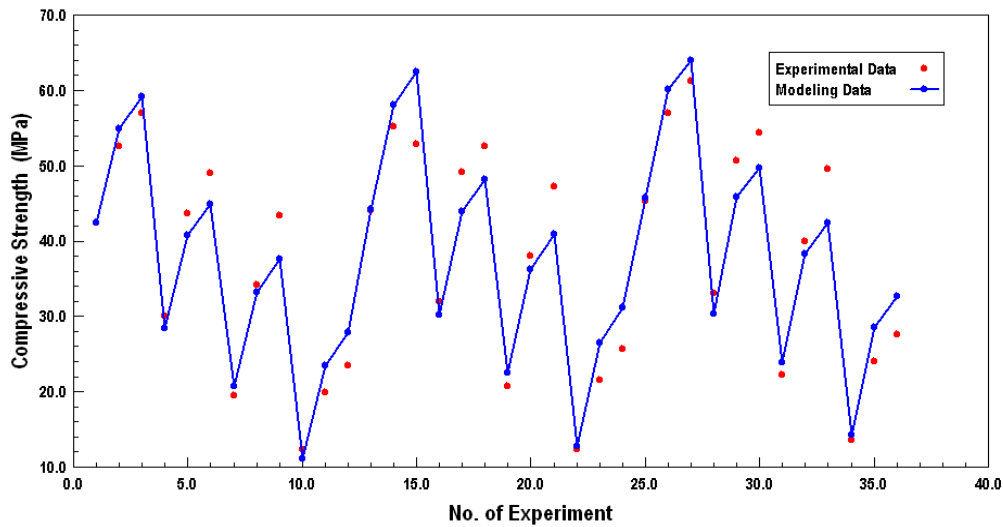


Figure 13: The difference between observed compressive strength and calculated compressive strength after burning in model (3).

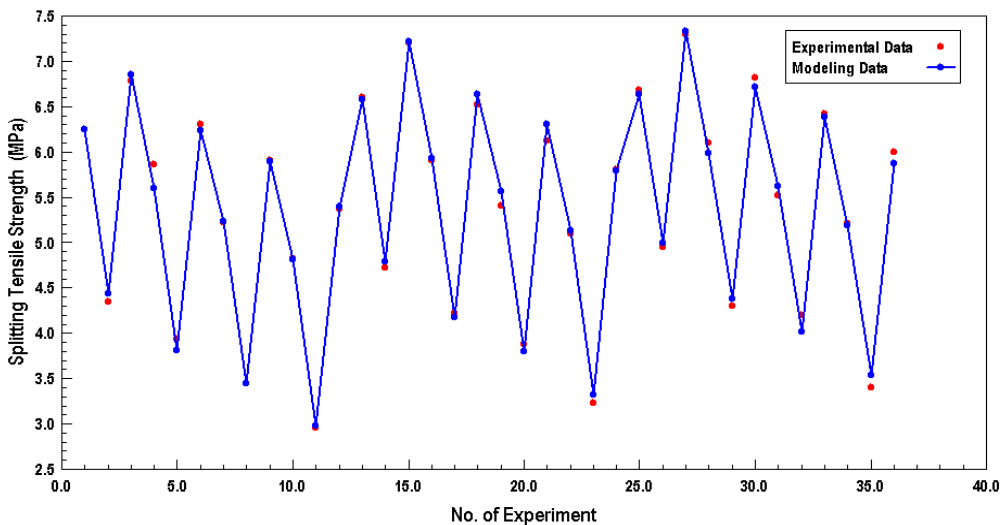


Figure 14: The difference between observed splitting tensile strength and calculated splitting tensile strength after burning in model (3).

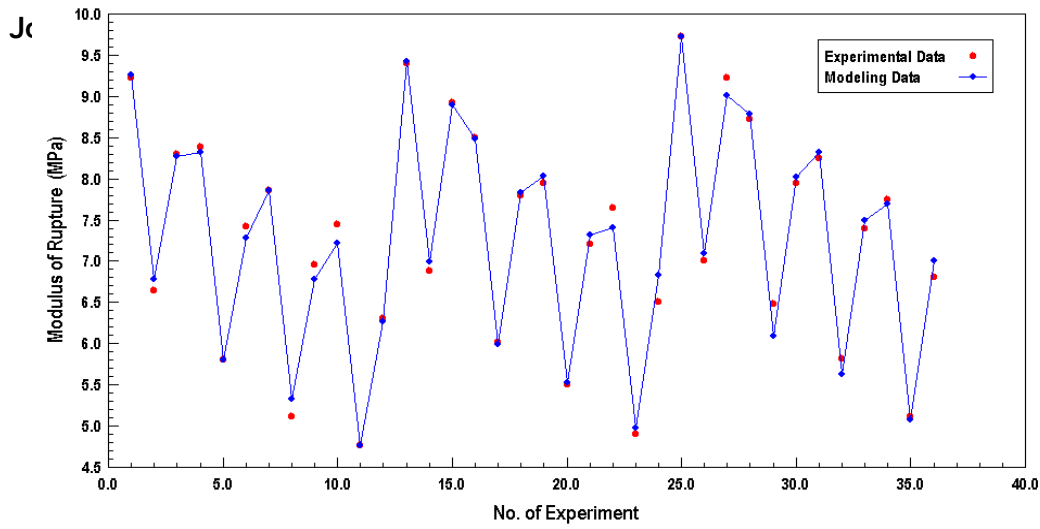


Figure 15: The difference between observed modulus of rupture and calculated modulus of rupture after burning in model (3).

-Conclusions

Based on the results of this experimental the following conclusion can be made :

- 1- The density, compressive, tensile and flexural strength of high strength concrete decrease with increasing fire flame temperature for all mixes and for all ages.
- 2- The splitting tensile strength is more sensitive to fire flame exposure than the compressive strength for all mixes and ages.
- 3- The flexural strength is more sensitive to fire flame temperatures than compressive strength and splitting tensile strength for all mixes and ages.
- 4- It was found that the loss in density of mix 3 less than that in density of mixes 1 and 2.
- 5- For the studied temperature range in this study, the compressive strength-reduction curve, recommended by the Euro codes CEN (1993, 1994) is in better agreement with the test results rather than CEB (1991) strength-reduction curve.
- 6- Concrete with silica fume suffered the most under increased exposure to fire flame temperature below 850 °C.
- 7- High-strength concrete has shown 74% drop in its strengths once exposed to 850°C irrespective of the type of binder materials used.
- 8- The reduction in tensile strength for high-strength concrete mixes was (78-84 %) when they were burned to 850°C.
- 9- Based on experimental results, an equation to estimate the compressive strength, splitting tensile strength and flexural strength of concrete after burning was suggested as follows:

$$f_{cua} = 1.21525 \times f_{cub} - 0.005178 \times Age - 0.039796 \times T - 0.00470 \times p + 3.423845$$

$$f_{sa} = 0.98577 \times f_{sb} - 0.00097 \times Age - 0.001541 \times T + 0.00560 \times f_{cub} - 0.081183$$

$$f_{ra} = 0.92504 \times f_{rb} + 0.00043 \times Age - 0.002841 \times T - 0.00986 \times f_{cub} + 1.21353$$

These equations gave a good agreement with the tested values in the experimental work.

-Reference

- **Abrams, M.S (1971)**, "Compressive Strength of Concrete at Temperature to 1660°F", ACI Special Publication Sp25, USA, pp.33-58.
- **AL-Ausi, M.A. and Faiyadh, F.I., 1985**, "Effect of Method of Cooling on The Concrete Compressive Strength Exposed to High Temperature ", Engineering and Technology , Vol.1.
- **Al-Owaisy, S., Rashid., (2001)**, "Effect of Elevated Temperatures on Bond in Reinforced Concrete", M.Sc. Thesis, College of Engineering, Department of Civil Engineering, Al-Mustansiriyah University, Baghdad, February, 107PP.
- **Comities Euro-International Du BETON (CEB). (1991)**, "Fire Design of Concrete Structures in Accordance With CEB / FIP Model Code 90", CEB Bulletin D' Information, Lausanne, Switzerland, 208 Cruz, C. R.
- **Committee Europe'en de Normalization (CEN). (1994)**, "Eurocode 4 : Design of Composite Steel and Concrete Structures. Part 1-2: General Rules of Structural Fire Design", Rep. No. CEN ENV.
- **Davis, H.S., (1967)**, "Effect of High Temperature Exposure on Concrete", Material Research and Standards, pp.452- 459.
- **Essa, M.S., (1999)**, "Effect of Burning by Fire Flame on Properties of Concrete", Journal of Babylon University, Series E, Engineering Science, Vol.4, No.5, October, pp. 1192-1202.
- **Faiyadh, F.I., and Al-Alusi, M.A., (1989)**, "Effect of Elevated Temperature on Splitting Tensile Strength of Fibre Concrete", The International Journal of Cement Composite and Lightweight Concrete, 11(3), pp.175-178.
- **Habeeb, G.M., (2000)**, "Residual Mechanical Properties of High Strength Concrete Subjected to Elevated Temperature", PhD Thesis, College of Engineering, Department of Civil Engineering, Al-Mustansiriyah University, Baghdad, Iraq, November, 164pp.
- **Husem, M., (2006)**, "The Effect of High Temperature on Compressive and Flexural Strengths of Ordinary and High-Performance Concrete" Fire Safety Journal 41:155-163.
- **Kadhum, M.M., (2010)**, "Behavior of Fire Exposed of Reinforced Concrete Columns", PhD Thesis, College of Engineering, Department of Civil Engineering, Baghdad University, Baghdad, Iraq, May, 198pp.
- **Karim, M.M., (2005)**, "Investigation of The Behavior and Properties of Reinforced Slabs Exposed to Fire Flame", M.Sc. Thesis, College of Engineering, Department of Civil Engineering, University of Babylon, December, 126pp.

- **Khoury, G.A., (1992),** "Compressive Strength of Concrete at High Temperatures", A Measurement Magazine of Concrete Research, 44(161), pp.29-309.
- **Malhotra, H.L., (1956),** "The Effect of High Temperature on Compressive Strength", Magazine of Concrete Research, 8(3) pp.85-94.
- **Noumowe, A.N., Clasters, P., Debicki, G., and Boluin, M., (1994),** "High Temperature Effect on High Performance Concrete (70-600°C) Strength and Porosity ", ACI Special Publication SP145, pp. 154-172.
- **Saqier, A.A., (1984),** "Effect of Fire Flame Exposed on Flexural Behavior and Shear Strength of Reinforced NSC and HPC Beams", M.Sc. Thesis, College of Engineering, Department of Civil Engineering, University of Babylon, December, 124pp.
- **Shetty, M.S., (1988),** "Concrete Technology", Theory and Practice, Third Edition, pp.361.
- **Sri Ravin Drarajah, R. and Mercer, C.M., (1993),** "Properties of High Strength Concrete Containing Cement Supplementary Materials", Proc. FIP Congress, Kyoto, Japan.
- **Sri Ravin Drarajah, R., and Stathopoulos, F., (1998),** "Residual Compressive Strength and Tensile Strength for High Strength Concrete Exposed to High Temperature up to 800°C", Proceeding International Conf. on High Performance High Strength Concrete, Perth, Australia, pp 663-645.
- **فهيمي، هاني محمد و أسعد، محمد باسم: 1991** "مقاومة وتصرف الخرسانة المسلحة المعرضة للحرارة العالية"

العدد الخامس، ٦، المجلد العاشر، الهندسة والتكنولوجيا، العراق-الجامعة التكنولوجية.