



وزارة التعليم العالي والبحث العلمي
جامعة ميسان
كلية التربية الاساسية

Ministry of Higher Education and Scientific
Research
University of Misan
College of Basic Education

Misan Journal for Academic Studies
Humanities, social and applied sciences

مجلة ميسان للدراسات الأكاديمية العلوم الانسانية والاجتماعية والتطبيقية

ISSN (Print) 1994-697X
(Online)- 2706-722X

المجلد 24 العدد 54 حزيران 2025

Vol 24 Issue 54 June 2025



مجلة ميسان للدراسات الأكاديمية

العلوم الإنسانية والاجتماعية والتطبيقية

كلية التربية الأساسية / جامعة ميسان / العراق

Misan Journal for Academic Studies

Humanities, social and applied sciences

College of Basic Education/University of Misan/Iraq

ISSN (Print) 1994-697X (Online) 2706-722X

حزيران 2025

العدد 54

المجلد 24

June 2025

Issue 54

Vol 24




INTERNATIONAL
STANDARD
SERIAL
NUMBER
INTERNATIONAL CENTRE

OJS / PKP

www.misan-jas.com

IRAQI

Academic Scientific Journals

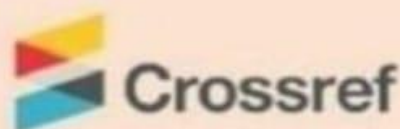

ORCID

OPEN ACCESS




journal.m.academy@uomisan.edu.iq

رقم الأيداع في دار الكتب والوثائق بغداد 1326 في 2009

الصفحة	فهرس البحوث	ت
8 - 1	Determine the bacterial resistance of Streptococcus sobrinus to antibiotics Hanan Saleh Abdulhussain Mithal K.A. Al-Hassani	1
20 - 9	Incidence, pattern and management of mandibular fractures in Al-Anbar governorate in 100 patients Sama Abdulsattar Abd Kamal Turki Aftan	2
29 - 21	Evaluation of salivary IL33 and IL37 in Periodontitis patients with and without type 2 diabetes mellitus Fadya Basil mejbel Heba Fadhil Hassan	3
46 - 30	The Impact of the Waterfall Technique on Spelling Accuracy and Vocabulary Retention among Primary EFL Learners Afrah Munshid Lahad	4
57 - 47	Salivary biomarkers of oxidants and antioxidants for chronic renal disease in patients undergoing maintenance hemodialysis Geehan Nazar Ali Layla Sabri Yas	5
74 - 58	Early detection and segmentation of asphalt pavement cracks: Iraqi highways as case study Shemeam T. Muhey Sinan A. Naji	6
91 - 75	Buzzwords in English Parliament Elections Atyaf Hasan Ibrahim, Narjis Audah Rashk Fatima Raheem Almosawi	7
108 - 92	Strategic Planning to Improve Creativity Using Artificial Intelligence for Islamic University of Minnesota Students USA Raed Mohammad Hanan Sobhi Abdullah Obaid Mohammed Arab Almusawi Helwe jaber Qusquse Fatima Abdurrahman Al-Maraghi	8
116 - 109	The Effect of Crown Fabrication Materials on Wear Resistance and Retention Strength: An Experimental Study Using Statistical Analysis and Magnetic Resonance Imaging Huda Jaafar Naser	9
122 - 117	Structural and Optical Properties of Copper Oxide Nanoparticles Synthesized by Chemical Precipitation Method Uday Ali Sabeeh Al-Jarah	10
145 - 123	Exploring Ideological Positioning in Barack Obama's Speech on Same-Sex Marriage: An Appraisal Theory Analysis Adawiya Jabbar Kadhim Ali Abdulhameed Faris	11
164 - 146	Evaluating the Government Hospitals' Efficiency and Their Impact on Human Development in Iraq Wafaa Hasan Jabur Luma Abdul Manaf Raheem	12
174 - 165	Enzymatic activity of fungi isolated from Otomycosis Azhar Lilo Sayyid Ali A Kasim	13


196 - 175	The Reality of Primary School Teachers' Practice of Professional Accreditation Standards in Light of Approaches to Teacher Professionalization from the Supervisors' Point of View Amera Ali Hasoon Ghasan Kadhim Jabber	14
212 - 197	The relationship of abrogation between the Qur'an and the Sunnah Ali Dhaigham Taher	15
230 - 213	Visual Art Methods and Techniques in Contemporary Art - American Painting as a Model Bayad Abdullah Faqi Ameen Nemat Mohammed Redha Hussein	16
245 - 231	Word-Displacement in The Poetry of Alsa'aleek "Vagabonds" (Selected Examples) Maitham Raheem Shaghathi	17
259 - 246	The deficiency of language in perspective the martyr Muhammad Al-Sadr in the book of Menna Al-Mannan in Defense of the Qur'an. Salem Rahim Maaleh	18
272 - 260	The Employment of Historical Symbolism by the Poets of the Seventies Generation:(Khazal Al-Majidi as a Model) Nadam JAbbar Nassr	19
304 - 273	The Level of Employing Professional Technical Skills by Art Education Teachers in Integrating the Relationship Between the Sciences and the Arts, from the Perspective of Specialty Supervisors Zainab Abdul Hussein Jaber Ammar Jabbar Hussein Al-Wahaj Ghassan Kazim Gabr	20
321 - 305	The Impact of a Teaching Strategy Based on TRIZ Theory on Developing Higher-Order Thinking Skills Among Gifted Students in Mathematics Saja Hussein Koma Alaa Ali Hussein	21
335 - 322	The poetic image in the Diwan of Al-Oqaisher Al-Asadi Faten Rajeh Abdel Hameed	22
345 - 336	The efficiency of some Iraqi clays in adsorbing lead using miscible displacement method Abathur Sabar Khalaf Hashim Haneen Kareem Mahdi Wasmy Soheib	23
365 - 346	Effectiveness of the Innovative Matrix Strategy in the Achievement of Students in the Department of Artistic Education in the Subject of Arabic Calligraphy Multaqqa Nassir Jabbar	24
377 - 366	The Intertextuality in Modern Novel: a case study in its origins, manifestations, and Interpretation Raed Radhi Bkheet	25



ISSN (Print) 1994-697X
ISSN (Online) 2706-722X

DOI:
<https://doi.org/10.54633/2333-024-054-010>

Received:26/Feb/2025
Accepted:25/Mar/2025
Published online:30/June/2025



:Structural and Optical Properties of Copper Oxide Nanoparticles Synthesized by Chemical Precipitation Method

Uday Ali Sabeeh Al-Jarah

Department of Science, College of Basic Education, University of Misan,
Misan, Iraq.

drudayaaljarah@uomisan.edu.iq

<https://orcid.org/0000-0002-1349-5116>

Abstract:

Sodium bicarbonate was used as a precipitation agent and copper nitrate as a precursor in the chemical precipitation process to create copper oxide nanoparticles (CuO-NPs). After that, scanning electron microscopy (SEM), X-ray diffraction (XRD), and ultra-violet (UV) microscopy have been used for characterizing the NPs. The prepared CuO-NPs showed crystalline and nanosize XRD patterns. The 26 nm crystallite size of the CuO NPs is confirmed by Scherer's formula. According to the SEM image, the NPs have been spherical and tended of agglomerations. Copper oxide absorption spectrum at about 270nm is confirmed by the UV-visible.

Keywords: copper nitrate, copper oxide, scanning electron microscope, X-ray diffraction, uv-visible spectroscopy.

INTRODUCTION:

The crucial pioneering role that nanotechnology played in modifying materials at the molecular and atomic level to significantly change the attributes of the final product attracted a lot of attention. When materials are lowered to the nanometric scale, their characteristics differ greatly from those at the microscale or macroscale. Nanomaterials are majorly employed in many different applications due to their special qualities. NPs in trace concentrations could be extremely important for the development of a material's characteristics. Because they are useful in so many different scientific domains, NPs are becoming more and more significant every day. Generally speaking, NPs range in size from 1 to 60 nm. Designing, building, and using functional structures having at least one characteristic dimension measured in nanometers is referred to as nanotechnology. Nowadays, NPs are used extensively in a variety of fields (Ahamed et al., 2014; Anandan et al., 2007, Khan et al., 2013; Kida et al., 2007; Kim et al., 2008; Manimaran et al., 2014; Mustafa et al., 2013; Suleiman et al., 2013; and Zhang et al., 2014). With a narrow band gap (e.g., 1.2eV), cupric oxide (CuO) is a significant transition metal oxide serving as foundation for a number of intriguing high temperature superconductors and enormous magneto resistance

materials (Jianliang et al, 2011). CuO is widely employed in several different applications, including gas sensor (Kaneshiro et al., 2010), macroscale (Yang et al., 2007), catalysis (Huang et al., 2009), and solar energy (Jianliang et al., 2011). Yet, synthesis of CuO nanostructures, which had demonstrated better performance compared with their bulk equivalents, could enhance such new features. A variety of CuO nanostructures are created, including nanowires, nanorods, nanoneedles, nanoflowers, and NPs. CuO NPs of different shapes and sizes were produced in recent decades using a variety of techniques, including thermal oxidation (Wu et al., 2010; and Zhu et al., 2004), quick-precipitation (Kaur et al., 2006), combustion (Narongdet et al, 2011), and sonochemical (Yamukyan et al., 2008). The precipitation approach is one of such simple procedures that has garnered a lot of interest from companies due to its low energy and temperature requirements, low cost, and high yield for large-scale production.

Experimental method:

Sodium bicarbonate solutions (0.1M) and copper nitrate (0.1M) have been made in distilled water as part of the chemical precipitation process used to create copper oxide. In order to keep the pH at 6.8, the sodium bicarbonate solution has been added drop by drop to the copper nitrate while stirring constantly. The reaction was then allowed to continue for two hours until all of the sodium bicarbonate had been added. Following the completion of the reaction by testing the entire precipitation, the precipitate was let to settle overnight before being filtered out and repeatedly cleaned with distilled water to remove any remaining excess bicarbonate. After noticing a pale blue precipitation, the supernatant solution was cautiously disposed of. The solution was cleaned, dried for five hours at a temperature of 100°C, and after that calcined for four hours at a temperature of 450°C.

Structural Analysis:

X- ray diffraction:

XRD spectrum of CuO NPs is displayed in fig 1, and it is evident that both broad and sharp peaks are present, indicating that the resulting CuO products have been formed in a mixed phase of amorphous as well as crystalline states. According to the JCPDS data card (89-2529) (Phiwdang et al., 2013), the peaks of diffraction at $2\theta = 32.06^\circ$, 35.48° , 38.74° , 48.71° , 61.53° , and 66.07° correspond to the (110), (111), (200), (202), (113), and (311) crystal planes of cubic phase CuO. With the use of Debye Scherrer's equation, the CuO nanocrystals' crystallite size has been calculated from a more intense peak in XRD spectra. The highly intense plane of (111) has an average crystallite size of 25 nm which was calculated by using the Debye-Scherrer equation (Ali et al., 2018; Al-Jarah et al., 2024).

$$D = k\lambda / \beta \cos \theta \quad (1)$$

"Where, D is the average crystallite size, k is constant = 0.9, λ is the wavelength of X-ray radiation (Cu $K\alpha=1.5406 \text{ \AA}$), β is the full width at half-maximum (FWHM), θ is the Bragg angle 2θ ".

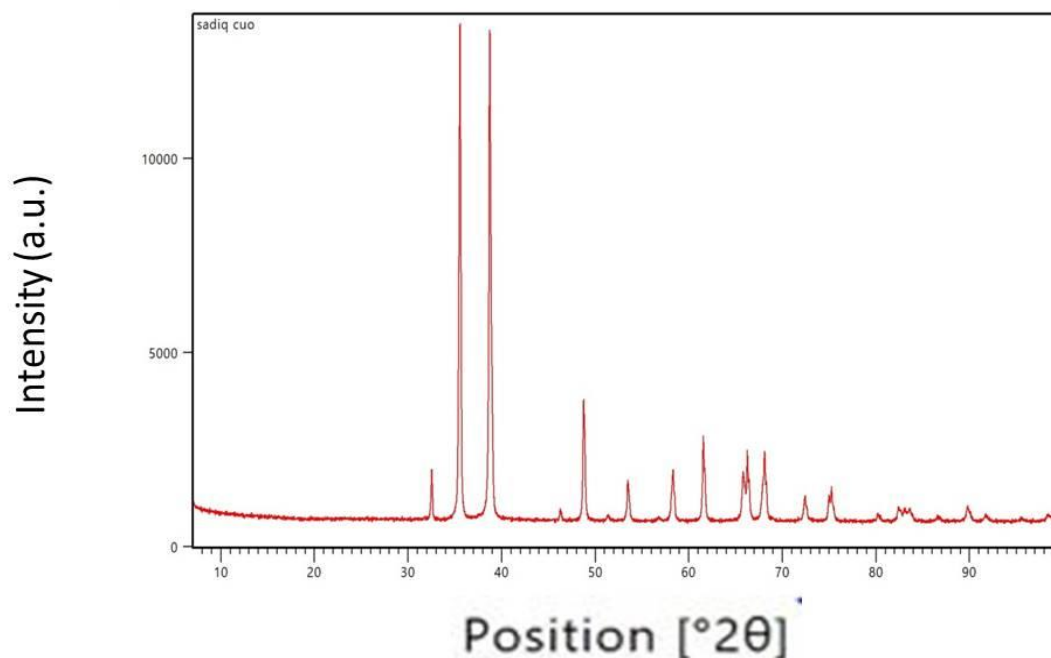


Fig (1): X-Ray diffraction of CuO nanoparticles

Scanning electron microscopy:

SEM study of the surface morphology of the copper oxide nanoparticles made with copper nitrate is depicted in fig 2. It demonstrates the existence of roughly shaped, yet varying-sized NPs with rough aggregate surfaces. According to the SEM scale, the size of crystalline CuO NPs ranged from 40 to 55nm, and the images showed that the particles were cuboid.

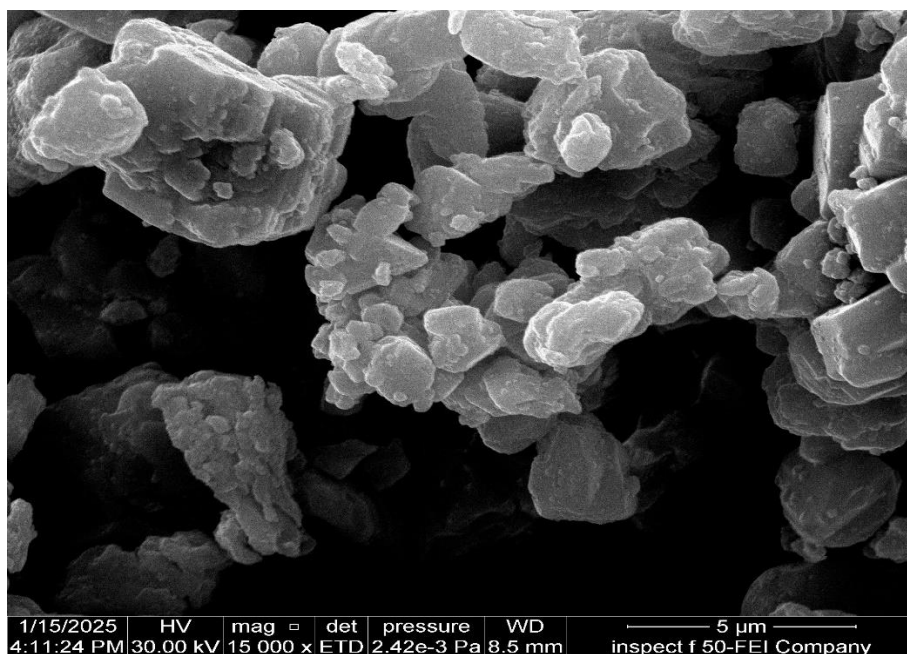


Fig (2): Scanning electron microscopy of CuO nanoparticles

UV- VISIBLE:

The optical characteristics of the produced CuO NPs were investigated using the optical absorption spectrum (Ragunath et al., 2021). Fig 3 displayed the copper oxide NPs's UV-vis absorption spectra. The formation of cuprous oxide NPs is responsible for the absorption peak at 270 nm in UV visible spectra, which is in good agreement with previous observations.

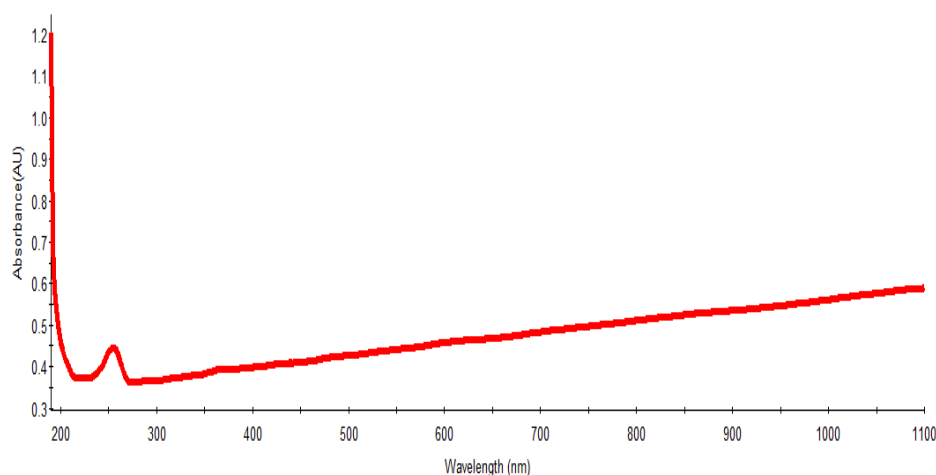


Fig (3): Absorbance spectra as a function of wavelength for of CuO nanoparticles

Conclusions:

Copper nitrate was used in the chemical precipitation process to create copper oxide NPs. XRD data, which displays all peaks with particle sizes of 26 nm, was used to confirm the structure regarding the CuO NPs. Using UV-visible spectroscopy; the optical characteristics of CuO NPs were examined.

Referances:

- Ahamed, M., Alhadlaq, H.A., Khan, M., Karuppiiah, P. and Al-Dhabi, N.A. (2014). Synthesis, Characterization, and Antimicrobial Activity of Copper Oxide Nanoparticles. *Journal of Nanomaterials*, 3, 33-42. <https://doi.org/10.1155/2014/637858>.
- Ali, M. M., Mahdi, H. S., Parveen, A., and Azam, A. (2018). Optical Properties of Cerium Oxide (CeO₂) Nanoparticles Synthesized by Hydroxide Mediated Method, *AIP Conf. Proc.*, 1953, 1, 030044. <https://doi.org/10.1063/1.5032379>.
- Al-Jarah, U. A., and Mahdi, H. S. (2024). Structural and Optical Properties of Co doped CdS Nanoparticles Synthesised by Chemical Method. *Misan Journal of Academic Studies*, 23(49), 153-157. <http://www.misan-jas.com/index.php/ojs/article/view/579>.
- Anandan, S. and Yang, S. (2007). Emergent Methods to Synthesize and Characterize Semiconductor CuO Nanoparticles with Various Morphologies—An Overview. *Journal of Experimental Nanoscience*, 2, 23-56. <https://doi.org/10.1080/17458080601094421>.
- Huang, B., Yeh, C., Wang, D., Tan, J., and Sung, J. (2009). Field Emission Studies of Amorphous Carbon Deposited on Copper Nanowires Grown By Cathodic Arc Plasma Deposition. *New Carbon Materials*, 24, 2, 97-101. [https://doi.org/10.1016/S1872-5805\(08\)60040-2](https://doi.org/10.1016/S1872-5805(08)60040-2).

- Jianliang C., Yan, W., Tianyi, M., Yuping Liu, Zhongyong Y. (2011). Synthesis of porous hematite nanorods loaded with CuO nanocrystals as catalysts for CO oxidation. *J Nat Gas Chem.*, 20, 6, 669-676. [https://doi.org/10.1016/S1003-9953\(10\)60238-1](https://doi.org/10.1016/S1003-9953(10)60238-1).
- Kaneshiro, J., Gaillard, N., Rocheleau, R., and Miller, E. (2010). Advances in copper-chalcopyrite thin films for solar energy conversion. *Solar Energy Materials and Solar Cells*, 94, 1, 12-16. <https://doi.org/10.1016/j.solmat.2009.03.032>.
- Kaur, M., Muthe, K., Despande, S., Choudhury, S., Singh, J., Verma, N., Gupta, S., and Yakhmi, J. (2006). Growth and Branching of CuO Nanowires by Thermal Oxidation of Copper. *J Cryst Growth*, 289, 2, 670-675. <https://doi.org/10.1016/j.jcrysgro.2005.11.111>.
- Khan, R.A., Beck, S., Dussault, D., Salmieri, S., Bouchard, J., and Lacroix, M. (2013). Mechanical and Barrier Properties of Nanocrystalline Cellulose Reinforced Poly (caprolactone) Composites: Effect of Gamma Radiation. *Journal of Applied Polymer Science*, 129, 3038-3046. <http://dx.doi.org/10.1002/app.38896>.
- Kida, T., Oka, T., Nagano, M., Ishiwata, Y. and Zheng, X.G. (2007). Synthesis and Application of Stable Copper Oxide Nanoparticle Suspensions for Nanoparticulate Film Fabrication. *Journal of the American Ceramic Society*, 90, 107-112. <http://dx.doi.org/10.1111/j.1551-2916.2006.01402.x>.
- Kim, Y.S., Hwang, I.S., Kim, S.J., Lee, C.Y. and Lee, J.H. (2008). CuO Nanowire Gas Sensors for Air Quality Control in Automotive Cabin. *Journal of Sensors and Actuators B: Chemical*, 135, 298-303. <https://doi.org/10.1016/j.snb.2008.08.026>.
- Manimaran, R., Palaniradja, K., Alagumurthi, N., Sendhilnathan, S. and Hussain, J. (2014). Preparation and Characterization of Copper Oxide Nanofluid for Heat Transfer Applications. *Applied Nanoscience*, 4, 163-167. <https://doi.org/10.1007/s13204-012-0184-7>.
- Mustafa, G., Tahir, H., Sultan, M. and Akhtar, N. (2013). Synthesis and Characterization of Cupric Oxide (CuO) Nanoparticles and Their Application for the Removal of Dyes. *African Journal of Biotechnology*, 12, 6650-6662. <https://doi.org/10.5897/AJB2013.13058>.
- Narongdet, W., Piyanut, C., Naratip, V., and Wisanu, P. (2011). Sonochemical Synthesis and Characterization of Copper Oxide Nanoparticles. *Energy Procedia*, 9, 404-409. <https://doi.org/10.1016/j.egypro.2011.09.044>.
- Phiwdang, K., Suphankij, S., Mekprasart, W., and Pecharapa, W. (2013). Synthesis of CuO Nanoparticles by Precipitation Method Using Different Precursors, *Energy Procedia*, 34, 740– 745. <https://doi.org/10.1016/j.egypro.2013.06.808>.
- Ragunath, L., Suresh, J., Sankaran, M., Kumar, R. S., Almansour, A. I., and Arumugam, N. (2021). Synthesis And Characterization Of Copper Oxide Nanoparticles Using Rambutan Peel Extract Via Greener Route, *Rasayan J. Chem.*, 14(4), 2660-2665. <http://dx.doi.org/10.31788/RJC.2021.1446512>.
- Suleiman, M., Mousa, M., Hussein, A., Hammouti, B., Hadda, T.B. and Warad, I. (2013). Copper (II)-Oxide Nanostructures: Synthesis, Characterizations and Their Applications—Review. *Journal of Materials and Environmental Science*, 5, 792-807. <https://www.jmaterenvironsci.com/Journal/vol4-5.html>.
- Wu, R., Ma, Z., Gu, Z., and Yang, Y. (2010). Preparation and characterization of CuO Nanoparticles with Different Morphology through a Simple Quick-Precipitation Method in DMAC-Water Mixed

Solvent. Journal of Alloys and Compounds, 504, 1, 45-49.

<http://dx.doi.org/10.1016/j.jallcom.2010.05.062>.

Yamukyan, M. H, Manukyan, K. V., Kharatyan, S. L., (2008). Copper oxide reduction by combined reducers under the combustion mode. Chemical Engineering Journal, 137, 3, 636-642. <https://doi.org/10.1016/j.cej.2007.05.033>.

Yang, Z., Xiuli, He., Jianping, L., Huigang, Z., Xiaoguang, G. (2007). Gas-sensing properties of hollow and hierarchical copper oxide microspheres. Sensors and Actuators B: Chemical, 128, 1, 293-298. <https://doi.org/10.1016/j.snb.2007.06.013>.

Zhang, W., Guo, F., Wang, F., Zhao, N., Liu, L. and Li, J. (2014). Synthesis of Quinazolines via CuO Nanoparticles Catalyzed Aerobic Oxidative Coupling of Aromatic Alcohols and Amidines. Journal of Organic and Biomolecular Chemistry, 12, 5752-5766. <https://doi.org/10.1039/C4OB00569D>.

Zhu, J., Li, D., Chen, C., Yang, X., Lu, L., Wang, X. (2004). Highly Dispersed CuO Nanoparticles Prepared by a Novel Quick-Precipitation Method. Materials Letters, 58, 26, 3324-3327. <https://doi.org/10.1016/j.matlet.2004.06.031>.

Conflicts of Interest Statement

Manuscript title:

Structural and Optical Properties of Copper Oxide Nanoparticles Synthesized by Chemical Precipitation Method

The authors whose names are listed immediately below certify that they have NO affiliations with or involvement in any organization or entity with any financial interest (such as honoraria; educational grants; participation in speakers' bureaus; membership, employment, consultancies, stock ownership, or other equity interest; and expert testimony or patent-licensing arrangements), or non-financial interest (such as personal or professional relationships, affiliations, knowledge or beliefs) in the subject matter or materials discussed in this manuscript.

Author names:

1. Dr. Uday Ali Sabeeh Al-Jarah

University of Maisan – College of Basic Education

The authors whose names are listed immediately below report the following details of affiliation or involvement in an organization or entity with a financial or non-financial interest in the subject matter or materials discussed in this manuscript. Please specify the nature of the conflict on a separate sheet of paper if the space below is inadequate.

Author names:

Dr. Uday Ali Sabeeh Al-Jarah

University of Maisan – College of Basic Education


This statement is signed by all the authors to indicate agreement that the above information is true and correct (a photocopy of this form may be used if there are more than 10 authors):

Author's name (typed)

Author's signature

Date

Dr. Uday Ali Sabeeh Al-Jarah



2025/3/18