

Photocatalytic Activity of Aluminum Oxide as A Catalyst for the Degradation of a Synthetic Azo Dye

Suad T Saad*, Hazim Y Al-Gubury, Nour Abd Alrazzak, and Nora Emad

Department of Chemistry, College of Science for Women, University of Babylon, Hilla, Iraq

*Corresponding author [e-mail: wsci.suaad.taha@uobabylon.edu.iq](mailto:wsci.suaad.taha@uobabylon.edu.iq)

Abstract

The photocatalytic degradation of the azo dye [3-((4-hydroxyphenyl) diazenyl)-4,5-dimethyl-1-phenyl-1,5-dihydro-2Hpyrrol-2-one][N1] was studied using aluminum oxide as a catalyst. The degradation process was performed at Rt, with a 125-watt mercury lamp as the external source. In this process, the impact of different amounts of aluminum oxide was tested, and the best degradation of the azo dye was achieved by using 0.12g of Al_2O_3 . The effect of dye concentration was also studied in the presence of the optimal amount of Al_2O_3 , with an optimal dye concentration of 20 ppm. For the entire process, the photodegradation efficiency was 82.78%.

Introduction

Water pollution is considered a life-threatening issue because it affects human life, animals, and aquatic ecosystems [1-3]. Various factors contribute to this issue. For example, domestic waste and factory waste [4,5]. The main materials discharged from factories are azo dyes, a widespread class of chemicals that enter water and lead to water pollution [6]. These dyes have been used in painting, cosmetics, and printing [7-9]. These dyes are characterized by their bright color, high solubility, and chemical stability [10,11]. Therefore, it is difficult to be degraded [12,13].

However, researchers have developed many techniques to solve this problem [14,15]. For example, chemical, physical, and biological techniques have been used [16]. One of the most effective chemical techniques is photocatalytic degradation using metal oxides as catalysts [17-19]. In this type of degradation, the metal oxide generates active free radicals during oxidation, which are responsible for dye degradation [20]. One of these interesting oxides is Al_2O_3 , which has been widely used due to its significant properties [21, 22].

In this work, Al_2O_3 was used to photocatalytically degrade a synthetic azo dye, and several parameters were investigated to assess the catalyst's photocatalytic activity.

2. Materials and Methods

The used azo dye and the photocatalytic degradation process were previously described in the literature [23, 24]. Al_2O_3 was supplied by Fluka (Buchs, Switzerland).

Result and Discussion

1- Effect of catalyst weight on the degradation process

Figure 1 shows the photocatalytic degradation of the azo dye using various quantities of Al_2O_3 . In this figure, the gradual increase in the catalyst weight leads to an increase in the photocatalytic degradation of this dye. However, the optimal catalyst weight was 0.12g/100ml. Beyond this amount, the photocatalytic degradation was decreased. Due to light scattering, which reduces the light reaching the lower solution layers, photocatalytic degradation is reduced [25-27].

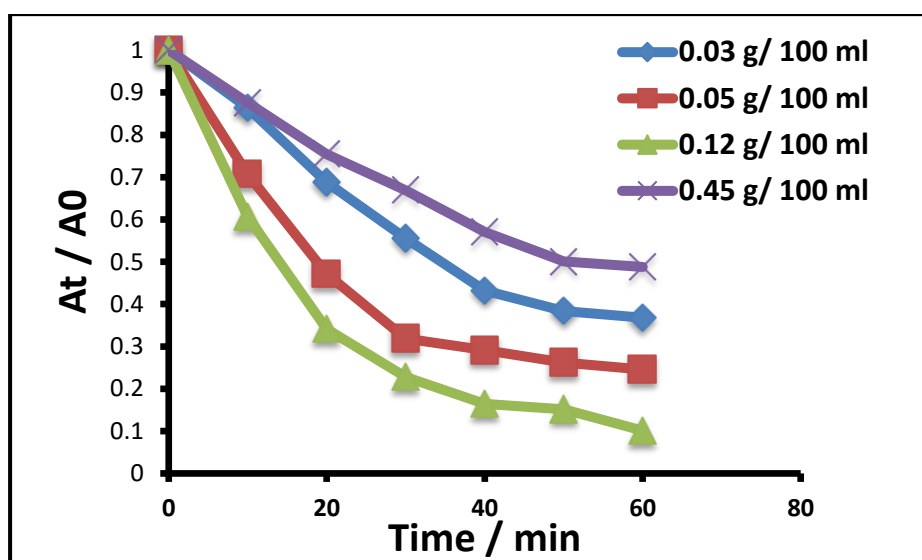


Fig. 1: Effect of Al_2O_3 weight on the azo dye photocatalytic degradation.

The kinetic analysis is shown in Figure 2. $\ln(A_0/A_t)$ was plotted against time, and the plot is linear through the origin. As a result, a first-order photocatalytic degradation was obtained.

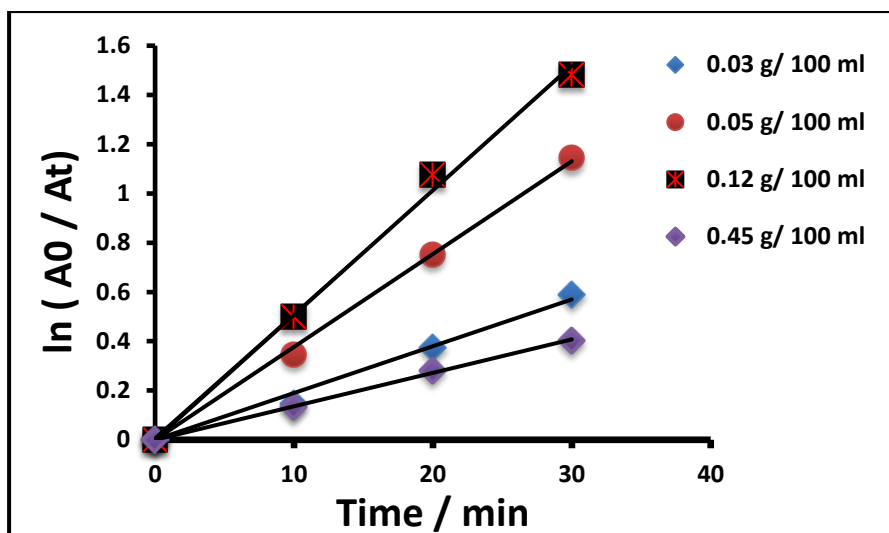


Fig. 2: Relationship between $\ln(A_0/A_t)$ and irradiation time.

2 - Effect of azo dye concentration

As mentioned before, various concentrations of the azo dye (20-50 ppm) were treated with a constant weight of Al_2O_3 (0.12 g). In Figure 3, the degradation rate decreased as the dye concentration increased. Where the best dye concentration was (20) ppm. When a high concentration of the azo dye is used, less photocatalytic degradation will be observed because less light penetrates the deeper layers of the dye solution [28-31].

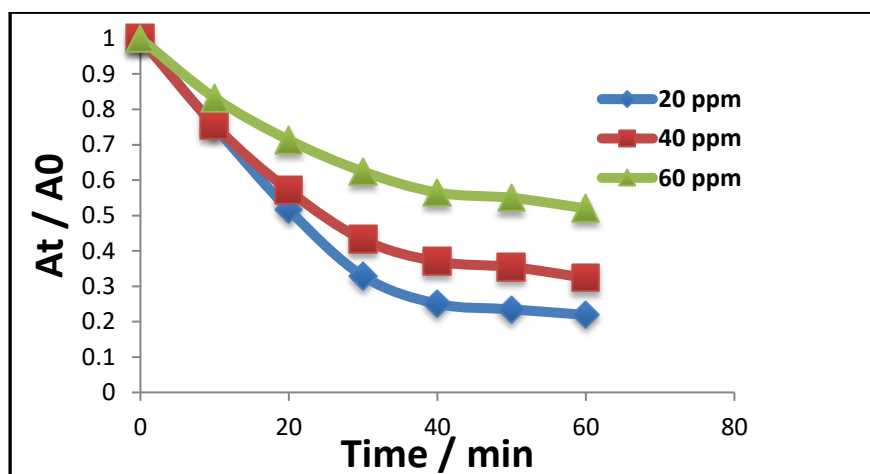


Fig. 3: Effect of dye concentration on the photocatalytic degradation at a constant weight of Al_2O_3

While the relation between $\ln(A_0/A_t)$ and time is linear, it agrees with the Langmuir-Hinshelwood model, as shown in Figure 4.

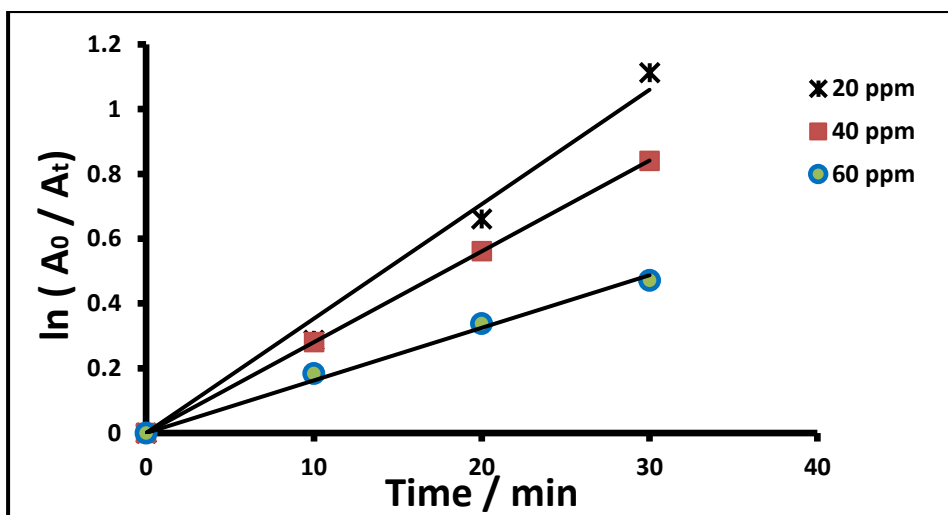


Fig.4: Relation between $\ln (A / A_0)$ with irradiation time at various concentrations of the dye

The highest photodegradation efficiency (PED), at the optimal dye concentration (82.78%), is shown in Figure 5.

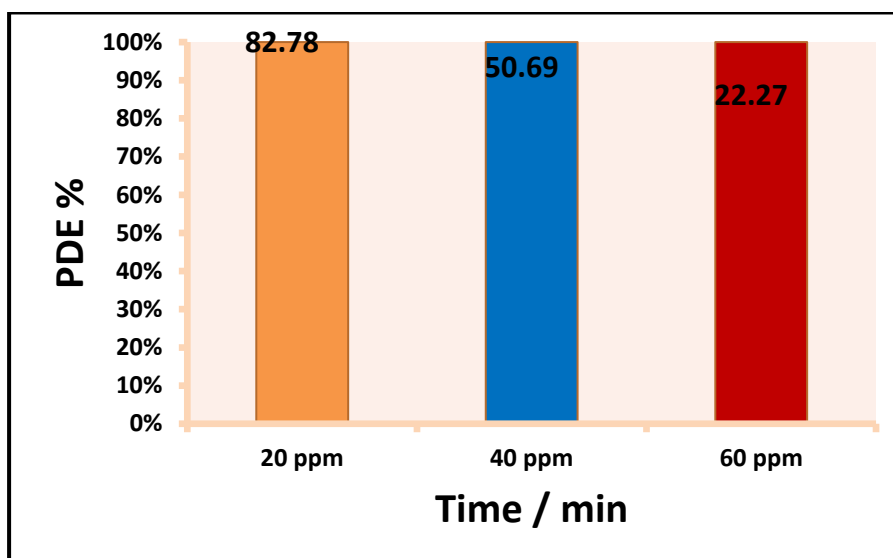


Fig.5: Photodegradation efficiency (PED) at various concentrations of the dye

Conclusion

The photocatalytic degradation activity of aluminum oxide was tested using the azo dye [3-((4-hydroxyphenyl) diazenyl)-4,5-dimethyl-1-phenyl-1,5-dihydro-2Hpyrrol-2-one][N1]. Various experiments have been conducted to determine the optimal conditions for the photodegradation

process. It was found that the catalyst exhibits a high photodegradation efficiency (82.78%) at the optimal dye concentration (20 ppm) and catalyst weight (0.12g/100 mL).

Acknowledgment

The authors would like to thank the Department of Chemistry, College of Science for Women, University of Babylon, for all the support in conducting this research.

References

- [1] M. Taghdiri, "Selective Adsorption and Photocatalytic Degradation of Dyes Using Polyoxometalate Hybrid Supported on Magnetic Activated Carbon Nanoparticles under Sunlight, Visible, and UV Irradiation" *Int. J. Photoenergy*, 2017, 2017, 1-15.
- [2] W. Hao, S. Ren, X. Wu, X. Shen, S. Cui, "Recent advance in the construction of 3D porous structure Ti₃C₂TX MXene and their multi-functional applications". *J. Alloys Compd.* 2023, 968.
- [3] Y-H Bae, S. Hong, J-S Noh, "Polythiophene/Ti₃C₂T_x MXene Composites for Effective Removal of Diverse Organic Dyes via Complementary Activity of Adsorption and Photodegradation", *Molecules*, 2025, 30, 1-18.
- [4] J. Li, X. Wen, Q. Zhang, S. Ren, "Adsorption and visible-light photodegradation of organic dyes with TiO₂/conjugated microporous polymer composites", *RSC Adv.*, 2018, 8, 34560–34565.
- [5] N. A. Mohammed, A. I. Alwared, M. S. Salman, "Photocatalytic Degradation of Reactive Yellow Dye in Wastewater using H₂O₂/TiO₂/UV Technique", *Iraqi j. chem. pet. Eng.*, 2020, 21, 15 – 21.
- [6] S.S. Shah, B. R. L. Ootubo, A. C. S.C. Teixeira, "Deep Removal and Photodegradation of Methylene Blue Dye Using Superabsorbent Polymer Hydrogel Composite with Activated Charcoal and TiO₂ Nanoparticles", *ACS Omega*, 2025, 10, 26441–26457.
- [7] E. Silveira, P. P. Marques, S. S. Silva, J. L. Lima-Filho, A. L. F. Porto, and E. B. Tambourgi, "Selection of Pseudomonas for industrial textile dyes decolourization," *Int. Biodeterior. Biodegrad.*, 2009, 63, 230–235.
- [8] W. A. Jabbar, M. F. A. Jabbar, "Study of Dyes and Methods of Their Removal, with a Focus on Studying Their Removal using Photocatalysts Based on Polyoxometalates: Review", *NJES* 2024, 27, 422-440.
- [9] N.M. Julkapli, S. Bagheri, S. B. Abd Hamid "Recent Advances in Heterogeneous Photocatalytic Decolorization of Synthetic Dyes", *Sci. World J.*, 2014, 2014, 1-25.
- [10] A. Saefumillah, B.S. Mahadika, Saepurahman, K.A. Kurnia, D.V. Wellia, D.O.B. Apriandanu, "Adsorption and photodegradation of various organic dyes in batch and flow systems over TiO₂-chitosan immobilized on glass beads", *results in surfaces and interfaces*, 2025, 18, 1-11.
- [11] V. L. E. Siong, K. M. Lee, J. C. Juan, C. W. Lai, X. H. Tai, C. S. Khe, "Removal of methylene blue dye by solvothermally reduced graphene oxide: a metal-free adsorption and photodegradation method", *RSC Adv.*, 2019, 9, 37686- 37695.

- [12] J. O. Quansah, T. Hlaing, F.N. Lyonga, P.P.Kyi, S-H. Hong, C-G Lee, S-J. Park,” Nascent rice husk as an adsorbent for removing cationic dyes from textile wastewater. *Applied Sciences* 2020, 10, 3437,1-16.
- [13] S. Khan, T. Noor, N. Iqbal, L. Yaqoob” Photocatalytic Dye Degradation from Textile Wastewater: A Review”, *ACS Omega*, 2024, 9, 21751–21767.
- [14] R. Al-Tohamy, S.S. Ali, F. Li, K.M. Okasha, A-G. Yehia, Y. A-G. Mahmoud, T. Elsamahy, H. Jiao, Y. Fu, J. Sun, “ A critical review on the treatment of dye-containing wastewater: Ecotoxicological and health concerns of textile dyes and possible remediation approaches for environmental safety. *Ecotoxicol. Environ. Saf.* 2022, 231, 113160.
- [15] I. Buta , M. A. Nistor, S. G. Muntean,” Efficient Photodegradation of Dyes from Single and Binary Aqueous Solutions Using Copper(II) Coordination Polymers,” *Molecules*, 2025, 30, 1-20.
- [16] M. Endashaw, T. Girma.” Review on the Removal of Dyes by Photodegradation Using Metal-Organic Frameworks Under Light Irradiation”, *Chem. Mater.*, 2020, 12, 2020,14-21.
- [17] C. Lydia, G. Allen Gnana Raj ,” A review on photodegradation of various dyes using photocatalysts, *IJASRM*, 2019, 4 , 37-42.
- [18] W. Cui, J. Y. Li, Y. J. Sun, H. Wang, G. M. Jiang, S. C. Lee, F. dong, *Appl. Catal., B*, 2018, 237, 938–946.
- [19] H. Wang, Y. Sun, G. Jiang, Y. Zhang, H. Huang, Z. Wu, S. C. Lee, F. Dong, *Environ. Sci. Technol.*, 2018, 52, 1479–1487.
- [20] H. Ayoub, M. Kassir, M. Raad, H. Bazzi, A. Hijazi”, Effect of Dye Structure on the Photodegradation Kinetic Using TiO₂ Nanoparticles”, *MSCE*, 2017, 5, 31-45.
- [21] S. Rajendran, G. Palani , V. Shanmugam , H. Trilaksanna , K. Kannan, M. Nykiel , K. Korniejenko., U. Marimuthu, “A Review of Synthesis and Applications of Al₂O₃ for Organic Dye Degradation/Adsorption”, *Molecules*, 2023, 28, 1-15.
- [22] B. Sharma, A. Sahi, J. Dhau, A. Kaushik, R. Kumar, G. R.Chaudhary,” Recycling waste aluminium foil to bio-acceptable nano photocatalysts [aluminium oxide (Al₂O₃) & aluminium oxyhydroxide (AlOOH)]; dye degradation as proof-of-concept”, *Mater. Adv.*, 2024, 5, 8304-8317.
- [23] N. Abd Alrazzak, S. T. Saad, E. J. Mohammad, M. M. Kareem, S. H. Kadhim,” Synthesis and Characterization of a New Azo Dye and Study of its Photodegradation on the Surface of Cobalt Oxide as a Catalyst,” *AIP Conf. Proc.* 2023, 2834, 1-5.
- [24] H. Y. Al-Gubury, S. T. Saad, N. Abd Alrazzak and R. M Naif,” Photocatalytic removal of eosin dye from aqueous solution over titanium dioxide,” *IOP Conf. Series: Materials Science and Engineering* , 2020, 871, 1-7.
- [25] R . Cucciniello, A. Intiso, T. Siciliano, A . E Palomares, J. Martínez-Triguero, J. L Cerrillo, A . Proto , F. Rossi ,” Oxidative Degradation of Trichloroethylene over Fe₂O₃-doped Mayenite: Chlorine Poisoning Mitigation and Improved Catalytic Performance”, *Catalysts*, 2019, 9, 1-13.
- [26] Q .Wang , K. Domen ,” Particulate photocatalysts for light-driven water splitting: mechanisms, challenges, and design strategies”, *Chemical Reviews*,2019, 120, 919-985.

- [27] H. Y Al-Gubury, N. Abd Alrazzak¹, S. T. Saad, S. Haider, "Photocatalytic removal of an azo dye from solutions using ZnO and modified ZnO: Benzoic acid azo dye as a model," IOP Conf. Series: Earth and Environmental Science, 2022, 1088, 1-8.
- [28] H .Y. Algubury," Study the activity of titanium dioxide nanoparticle using orange G dye," MJS, 2016, 35, 340-353.
- [29] M .A. Mahmood, J Dutta," Microwave assisted hydrothermal synthesis of zinc hydroxystannate films on glass substrates", J. Sol-Gel Sci. Technol., 2012, 62, 495-504.
- [30] K. Badvi, V. Javanbakht," Enhanced photocatalytic degradation of dye contaminants with TiO₂ immobilized on ZSM-5 zeolite modified with nickel nanoparticles. J. Clean. Prod.. 2021, 280,1-13.
- [31] H .Y. Al-Gubury, G.S. Al-Murshidy ," Photocatalytic decolorization of brilliant cresyl blue using zinc oxide", Int. J. PharmTech Re., 2015, 8, 289-297.